

IICBE INT'L CONFERENCE

INTERNATIONAL CONFERENCE ON CHEMICAL,
ENVIRONMENTAL AND BIOLOGICAL SCIENCES
[CEBS-2015]

MARCH 18-19, 2015 DUBAI [UAE]



Editors:

Prof. Dr. Rahim Ahmadi
Prof. Dr. Mariam Gaidamashvili

ISBN : 978-93-84422-11-0



Program Committee (CEBS-2015)

Conference Chair

Dr. Md. Aminur Rahman, Laboratory of Marine Biotechnology, Institute of Bioscience, University Putra Malaysia (UPM), Malaysia

Prof. Dr. Rahim Ahmadi, Department of Biology, Islamic Azad University, Hamedan Branch, Hamedan, Iran

Prof. Ihab H Farag, Sc.D., Chemical Engineering Dept., University of New Hampshire (UNH), Durham, NH, USA

Co-Chair

Assoc. Prof. Mariam Gaidamashvili, Department of Biology, Faculty of Exact and Natural Sciences, Javakhishvili Tbilisi State University, Georgia

Prof. Dr. P. S. Sandhu, Graphic Era University, Dehradun, India

Dr. Saji Baby, Environmental Manager (Research and Consultation) & Principal Scientist, GEO Environmental Consultation, Kuwait

Prof. Dr. Edison Muzenda, Department of Chemical Engineering, Faculty of Engineering and the Built Environment, University of Johannesburg, Doornfontein, Johannesburg

Technical Committee

Associate Prof. Dr. Moetaz El-Hawary, Associate Professor, Civil Engineering Department, Kuwait University, Kuwait

Prof. Dr. Fumihiko Isada, Professor, Graduate School of Health Care Sciences, Jikei Institute, Osaka, Japan

Prof. Dr. Takatoshi Ueno, Institute of Biological Control, Faculty of Agriculture, Kyushu University, Fukuoka, Japan

Prof. Dr. Cesar Demayo, Department: Biological Sciences, MSU-Iligan Institute of Technology, Philippines

Dr. Piotr F. Borowski, Warsaw University of Life Sciences, Warsaw, Poland

Prof. Mohammad Saquib, Professor, Adamawa State University, Mubi, Nigeria

Dr. Mansour Awiedat Salem, Associate Professor, Sebha University, Libya

Prof. Ayo Samuel Afolabi, Department of Civil and Chemical Engineering, University of South Africa– Unisa, Johannesburg, South Africa

Prof. Maybelle Gaballah, Water Relations and Field Irrigation Dept. National Research Centre, Cairo, Egypt

Prof. VA Sumanasinghe, Professor, Faculty of Agriculture, University of Peradeniya, Sri Lanka

Dr. Deirdre Dragovich, Associate Professor, School of Geosciences, University of Sydney, Sydney, Australia

Dr. Michael K. Bowen, Daystar University, Nairobi, Kenya

Prof. Dr. BULENT TOPCUOGLU, Environmental Protection and Control, Akdeniz University, Turkey

Assoc. Prof. Dr. Ismail Mohd Hasmadi, Faculty of Forestry, Universiti Putra Malaysia, Malaysia

Assoc. Prof. Dr. Pramod Kumar Gupta, Department: Department of Civil Engineering, IIT Roorkee, India

INDEX

International Conference on Chemical, Environmental and Biological Sciences (CEBS-2015) March 18-19, 2015 Dubai (UAE)

SECTION-I

Paper ID	Title of the Paper and Authors	Page No.
C0315030	<i>Effect of Root Architecture and Mycorrhizal Colonization on Growth and Cd Uptake by Two Species of Clover Plants</i> Habiballah Nadian, Siroos Jafari, and Tayebah Darvishi	1
C0315036	<i>Optimization of Oleyl Ester using Statistical Approach of Response Surface Methodology</i> Salina Mat Radzi, Mohd Akmal Rosli, Hanina Mohd Noor, and Maryam Mohamed Rehan	5
C0315037	<i>Protein Produced by Bacillus subtilis ATCC11774 after Inducing with Allium sativum Extract</i> Hanina Mohd Noor, Hairul Shahril Muhamad, Salina Mat Radzi, and Maryam Mohamed Rehan	10
C0315040	<i>Adsorptive Desulfurization of Commercial Diesel oil Using Granular Activated Charcoal</i> Isam Al Zubaidi, Noora Naif Darwish, Yehya El Sayed, Zarook Shareefdeen, and Ziad Sara	15
C0315046	<i>Probability Studies for Assessment of Dissolved Oxygen Profiles in Krishna River</i> Chandra Sekhar. M, Mahesh	19
C0315048	<i>Effect of Altitude on morphological characteristics of Euphorbia macrostegia</i> Mohammad mehdi Rahimi, and Maryam Bagheri	24
C0315049	<i>Effect of Ferula gommusa Essential oil controlling the Black Bean Aphid</i> Mohammad mehdi Rahimi, and Maryam Bagheri	27
C0315054	<i>Respiratory Health of the Workers on Wood Processing Industries on the Province of South Sumatra</i> Chairil Zaman, Tan Malaka, Ridhah Taqwa, Hatta Dahlan, and Fatmawati	31
C0315058	<i>Introduction of Alkyl Fatty Ether into the C3-Hydroxy Group of the Cholesterol</i> Fahima Ali-Rachedi	36
C0315059	<i>Synthesis of Curcumin Loaded CM CAB Nanoparticles for Treatment of Rheumatoid Arthritis</i> Ashish Kumar Dewangan, Sunil Varkey, and Sonal Mazumder	38

Paper ID	Title of the Paper and Authors	Page No.
C0315060	<i>Optimization of Product Parameters of Drug Loaded Polymeric Nanoparticles Prepared by Rapid Precipitation</i> Sunil Varkey, Ashish Kumar Dewangan, and Sonal Mazumder	44
C0315062	<i>Adsorption of the Methylene Blue from Aqueous Solution by the Thermally Regenerated Spent Bleaching Earth</i> Amir Heydari, Arezoo Merikhy, Habibollah Eskandari, Fardin Ghahraman-rozgar, and Moharam Ghamin	48
C0315073	<i>The Effect of The Electrode in Fluoride Removal from Drinking Water by Electro Coagulation Process</i> A. Takdastan, S. Emami Tabar, A. Islam, M.H. Bazafkan, and A.K Naisi	51
C0315074	<i>Survey on nanofiltration technology efficiency in Heavy metals (Ni, Cu and Zn) removal from waste water</i> SM. Daei Niaki, A. Takdastan, M.H. Bazafkan, and MA. Zazouli	57
C0315075	<i>Seed Germination Response of Medicago rigidula and Medicago polymorpha to KNO₃, Gibberellic Acid, Sulfuric Acid, and polyethylene glycol</i> Hossein Sadeghi, and Kamal Khani	62
C0315076	<i>Crop Straw Incorporated as a Strategy to Prevent Burning Straw Residues</i> Hossein Sadeghi	64
SECTION-II		
C0315079	<i>Determination of the Effect of Gypsum and Irrigation Water in Reclamation of Sodic Soils in South Khartoum</i> Salah Abdel Rahman Salih, Mohamed Abdel Mahmoud Elsheitk, and Azmi Elhag Aydrous	66
C0315080	<i>Survey of Poly Aluminum Chloride with Powdered Activated Carbon as Coagulant Aid in TOC Removal From Karoon River in Iran</i> M.H.Bazafkan, A. Takdastan, and A. Eslami	69
C0315084	<i>Water balance Simulation Model for Optimal Reservoir Sizing and Multi-crop Cultivation Area for Small Scale Water Harvesting in rainfed farming System at Khor Abu Farga - Gadarif -Sudan</i> Mohammed Abdelmahmood El shikh, Haitham R. Elramlawi, and Hassan I. Mohamed	75
C0315093	<i>Evaluation and Optimizing the Operating System of Aeration Tanks</i> Mohamed F. Soliman, Mohamed S. Dardear, Nashat A. Ali , S. A. Gutub, M. Bassyouni, and Mohamed A. Soltan	82
C0315097	<i>Removal of Pollutants from Freshwater Using Foam Biocomposites in a Fixed Bed Packed Column: Adsorption and Kinetic Study</i> Mohamed Bassyouni, Mohamed Abdel-Aziz, Saud Gutub, Mohamed Soliman, and Shereen Abdel-Hamid	87

Paper ID	Title of the Paper and Authors	Page No.
C0315099	<i>Comparative efficacy of Aqueous extract of Moringa (Moringa oleifera Lam.) and Coconut (Cocos nucifera L.) milk on the Performance of Pawpaw (Carica papaya L.) seedlings</i> M. A. Muhamman, and B. Kwada	93
C0315109	<i>Fabrication Process and Optimization of Hybrid MWCNTS/GF Reinforced Polypropylene</i> O. Al-Qabandi, Anjali De Silva, Salah Al-Enezi, and M. Bassyouni	96
C0315120	<i>Anaerobic Co-Digestion of Vegetable Waste and Cooked Oil in Anaerobic Sequencing Batch Reactor (ASBR)</i> J V Thanikal, M. Torrijos, S M Rizwan, Hatem Yazidi, R. Senthil Kumar, and Philipe Sousbie	101
C0315137	<i>Assessment of Noise pollution during Deepawali Festival in Raipur City of Chhattisgarh, India</i> Ajay Vikram Ahirwar, and Samir Bajpai	105
C0315003	<i>Dinoflagellate Cyst Assemblage and Marine Sediment Characteristics of Colombo Port, Sri Lanka</i> Dulanjali Wijethilake, and R R M K P Ranatunga	108
C0315012	<i>Study of the Impact of DNA Methylation on the Expression of Cell Cycle Regulators in Bladder Carcinoma</i> Mohamed Abd Ellatif, Raymonde H. Assaf, Fagr B. El-Shahat, Ahmed B. Shehab El-Din, and Salwa M. Abou El-Khair	113
C0315026	<i>Dithanolamine Functionalized Waste Tea Activated Carbon for CO₂ Adsorption</i> Manase Auta, Musa Umaru, Muibat Diekola Yahya[*], Olalekan David Adeniyi, Ibrahim Mohammed Aris, and Bilyaminu Suleiman	119
C0315027	<i>Photolytic Oxidation of Hazardous Organic Compound: Phenol</i> Parteek Singh Thind, Swapna Thomas, and Siby John	123
C0315032	<i>Removal of Turbidity and Coliform Bacteria from Karoon River water by natural Coagulants Aid (Bread Yeast) With PAC</i> Abdolkazem Neisi, Asghar Esteresh, Afshin Takdastan, and Naghmeh Orooji	128
C0315063	<i>Y Chromosome Microdeletions in Infertile Men from South West of Iran</i> Raheleh Masoudi, and Liusa Mazaheri-Asadi	133

Diethanolamine Functionalized Waste Tea Activated Carbon for CO₂ Adsorption

Manase Auta, Musa Umaru, Muibat Diekola Yahya, Olalekan David Adeniyi, Ibrahim Mohammed Aris, and Bilyaminu Suleiman

Abstract— Development of carbon (VI) oxide (CO₂) adsorbent was attempted by modifying mesoporous waste tea activated carbon (WTAC) with diethanolamine through impregnation. The modified and unmodified WTAC were used for selective adsorption of CO₂ from gaseous mixture (CO₂ and N₂). Effect of certain adsorption parameters such as concentration of the functionalizing agent (diethanolamine), column adsorption temperature, adsorbent dosage (bed height), concentration of the CO₂ in the feed and influent gas flow rate on breakthrough curves were evaluated. The exothermic nature of CO₂ capturing by MWTAC was physisorptive due to the increase in adsorption at lower temperature and the extra amine groups present. The optimum condition for CO₂ capturing by MWTAC were at adsorption column temperature of 30 °C, 10 % CO₂ feed concentration, 1.0 M of diethanolamine used for modification and influent feed flow rate of 90 mL/min. The result of this investigation shows that MWTAC is an excellent CO₂-phylic adsorbent.

Keywords— Adsorption, Carbon dioxide, Diethanolamine, Mesoporous activated carbon.

I. INTRODUCTION

PROLIFERATION of fossil fuel exploration in on the rise due to increase in demand and consumers of the products. But the associated emission of CO₂ during the fossil fuel processing and usage impacts negatively on the pristine global climate. According to Fisher [1], the use of fuel derived from coal, petroleum and natural gas for electricity generation and transportation purpose account for about 36% of CO₂ emission to the environment. The author further added that this source is the largest emitter of CO₂ to the atmosphere worldwide.

Manase Auta is with Federal University, Department of Chemical Engineering, Minna, Nigeria. (corresponding author's phone: +234(0) 8163532292 (e-mail: manaseauta@yahoo.com).

Musa Umaru, is with Federal University, Department of Chemical Engineering, Minna, Nigeria (e-mail:umar.musa@futumina.edu.ng).

Muibat Diekola Yahya is with Federal University, Department of Chemical Engineering, Minna, Nigeria (e-mail: muibat.yahya@futumina.edu.ng).

Olalekan David Adeniyi is with Federal University, Department of Chemical Engineering, Minna, Nigeria (e-mail: lekanadeniyi2002@yahoo.co.uk).

Ibrahim Mohammed Aris is with Federal University, Department of Chemical Engineering, Minna, Nigeria (e-mail: ma.ibrahim@futumina.edu.ng).

Bilyaminu Suleiman is with Federal University, Department of Chemical Engineering, Minna, Nigeria (e-mail: bilyaminusuleiman@yahoo.com).

Climate change, air toxics and ocean acidification are among the several other negative impacts faced with rise of CO₂ concentration in the entire ecosystem[2,3].

Several methods such as aqueous amine, adsorption, membrane separation, solid amine process amongst others have been employed for removing CO₂ from gaseous mixture. This is aside other measures like point source capture and sequestration processes put in place to alleviate its poisoning effect [1]. Among the numerous methods devised, adsorption stands out due to its simplicity, efficacy and affordability. The emergence of diverse adsorbents for capturing of CO₂ include examples of adsorbents like commercial activated carbons, molecular sieves, zeolite, clays amongst others have attracted investigation into the practicality, stability and design of full scale adsorption process [4]. More recently, efforts has been directed towards CO₂ capturing through functionalization of such adsorbents with amines, ammonia, base compounds and formation of composites [5]. This innovation has shown excellent CO₂ selectivity, high adsorption capacities and good adsorbent regeneration ability [2].

Amine modified adsorbents have been found to adsorb CO₂ molecules through chemical bond formation, pore diffusion, physical adsorption or physisorption (simultaneous physical and chemical) processes [6]. Chemical adsorption of CO₂ on amine (primary or secondary) modified sorbents principally gives rise to carbamate (thermally unstable due to its release of CO₂ at elevated temperature) and bicarbamate (further reaction of carbamate with CO₂ and water) [7]. In the presence of water molecules, stoichiometrically, one mole of CO₂ can chemically be bound to a mole of amine however, in dehydrated condition; a mole of CO₂ can adequately be chemisorbed on two moles of amine [3-4, 8-9]. To the best of the knowledge of the authors, there is no report on amine modified mesoporous waste tea activated carbon for CO₂ adsorption.

This research is aimed at synthesizing a cheap CO₂-phylic sorbent with high adsorption capacity by modifying mesoporous waste tea activated carbon with diethanolamine. The sorption capacity of different diethanolamine concentration was investigated and effect of column temperature, CO₂ feed concentration, Column adsorbent loading (bed-height) and feed flow rate on the breakthrough curves were examined.

II. MATERIALS AND METHOD

Carbon dioxide (99% purity) and Nitrogen gases were supplied by Whole sale gas company South Africa.

Diethanolamine and methanol were supplied by Sigma-Aldrich Company in South Africa.

Preparation of adsorbent for CO₂ adsorption

Waste tea activated carbon (WTAC) was prepared as described in our previous work [10]. Modification of the WTAC with diethanolamine was carried out in a similar method used in our previous work [11].

Ten grams (10 g) of the WTAC was added to 300 mL of 1.0 M diethanolamine (28 mL of diethanolamine plus 300 mL of methanol) and stirred for 5 h at room temperature. The WTAC and amine mixture was washed with methanol after filtration and then dried under vacuum at 70 °C for 6 h. The dried WTAC modified with diethanolamine (MWTAC) was packaged in air tight container for further use.

Fixed-bed column adsorption

The column adsorption experiment of CO₂ with the MWTAC was carried out in a similar method as reported in our previous work [11]. The effect of some adsorption parameters such as concentration of diethanolamine used for modification (0.5 to 1.5 M), percentage of CO₂ in the feed stream (10, 15 and 20%), gas influent flow rate (90, 120 and 150 mL/min), adsorbent dosage (2, 3 and 4 g) and column temperature (35, 45 and 55 °C) on the resulting CO₂ adsorption breakthrough curves were studied.

III. RESULTS AND DISCUSSION

Effect of column temperature on breakthrough curves

The temperature at which the MWTAC adsorb CO₂ optimally connotes whether the adsorbent is suitable for pre or post-combustion effluent discharge processes. Breakthrough profiles with respect to temperature variation are presented in Fig. 1. The result of the investigation revealed that adsorption of CO₂ by MWTAC was favoured at low temperature of 30 °C; the adsorption capacities (mg/g) and breakthrough time (seconds) were 53.62, 34.27, 23.46 (mg/g) and 900, 605, 410 (s) for 30, 40 and 50 °C, respectively. This showed that modification of the WTAC with diethanolamine did not affect the adsorbent properties which were earlier reported demonstrating exothermic behavior towards liquid the adsorbate from the thermodynamic studies [12]. The exothermic nature of MWTAC adsorbent towards CO₂ is similar to that of silica-templated melamine-formaldehyde resin derived for CO₂ capture [13]. The reduction in CO₂ capture at elevated temperature by MWTAC was attributed to instability of the adsorbate molecules due to increase in excitement with addition of more heat to the system. The presence of extra amine groups on the adsorbent surface may have also contributed to the physisorption of CO₂ [14]. The physisorption nature of the CO₂ adsorption on MWTAC revealed that the adsorbent requires little or no extra energy before its active sites are activated to function optimally [15].

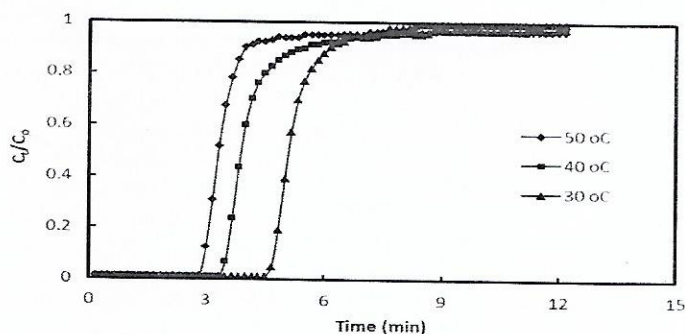


Fig.1 Adsorption column temperature variation effect on breakthrough curves at 10% CO₂ feed concentration (balance of N₂), 90 mL/min feed flow rate, 3 g adsorbent dosage, 1.0 M MWTAC particle sizes of 1-2 mm.

Effect of MWTAC adsorbent column loading on breakthrough curves

The breakthrough curves for the various masses of 1.0 M MWTAC were measured from the plot of C/C₀ (ratio of concentration of CO₂ in the fluid to that of the CO₂ in the influent feed) versus time. The effect of bed height on the breakthrough curves are presented in Fig. 2, at adsorbent column loading of 2, 3 and 4 g, the breakthrough time of 240, 900 and 970 s, and adsorption capacities of 19.83, 53.62 and 64.52 mg/g, respectively were obtained. The result of this study showed that high mass transfer was more pronounced at the inlet. This was obvious because the inlet point was the first point of contact between the inlet CO₂ gas and the adsorbent in the column. However, a gradual reduction in the mass transfer was observed with time as the sorbent became saturated [16]. At the breakthrough point, the adsorbent is saturated and the mass transfer zone (S-shaped) gradually moves away from the inlet until it attains equilibrium with the feed. It can be seen from Fig. 2 that the more the mass (bed height) of the 1.0 M MWTAC used in the column, the longer the breakthrough time and adsorption capacity. This observation is in accordance with the expected trend [17].

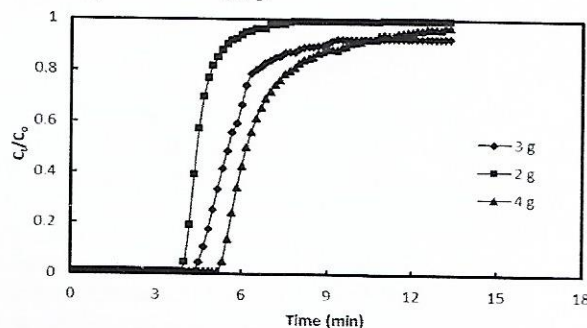


Fig. 2 Adsorbent dosage (bed-height) effect on breakthrough curves at 10 % CO₂ feed concentration (balance of N₂), 90 mL/min feed flow rate, 3 g adsorbent dosage, 1.0 M MWTAC particle sizes of 1-2 mm, 30 °C adsorption column temperature.

Effect of feed flow rate on breakthrough curves

Variation of feed flow rate was directly proportional to the quantum of the gas molecules contacted the surface of the MWTAC adsorbent. The resultant profiles of the flow rate

variation are shown in Fig. 3. Rapid attainment of breakthrough point (135 s) was observed at high feed flow rate (150 mL/min) which was attributed to fast preponderance of numerous molecules contact to the static or inelastic vacant sites of the adsorbent. Whereas, gradual and longer time of breakthrough point (900 s) attainment was associated with the low feed flow rate (90 mL/min). Low feed flow rate may have created or given room for ample residence time thereby enabling chronological adsorption of CO₂ molecules enormously. It has also been observed by other researchers also that concurrent reduction of CO₂ adsorption and breakthrough time occurs at higher influent flow rate of the gas [18].

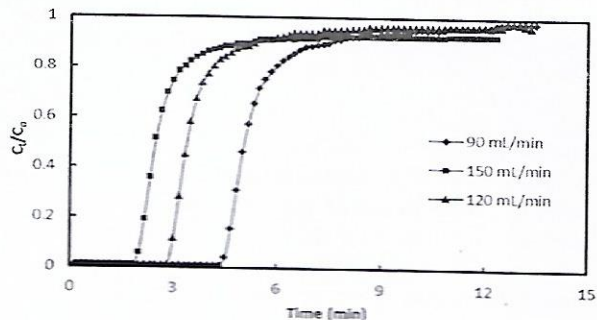


Fig. 3 The effect of Feed flow rate variation on breakthrough curves at 10% CO₂ feed concentration (balance of N₂), 3 g adsorbent dosage, 1.0 M MWTAC particle sizes of 1-2 mm, 30 °C adsorption column temperature

Effect of diethanolamine concentration used for modification on the adsorbent activities

Adsorption activities of the unmodified and modified waste tea activated carbon were evaluated for CO₂ capturing and the breakthrough profiles of the evaluation are presented in Fig. 4. The use of 0.5, 1.0 and 1.5 M diethanolamine functionalizing agent for modification and use of un-functionalized adsorbent (UWTAC), gave corresponding adsorption capacities of 33.57, 53.62, 46.23 and 20.07 mg/g, respectively. The modified waste tea activated carbon with diethanolamine (MWTAC) adsorbent, exhibited longer breakthrough curves and better adsorption of the CO₂ than the unmodified waste tea activated carbon (UWTAC). The introduction of the extra amine groups on the WTAC surfaces enhanced attraction of the negative CO₂ molecules to the adsorbent surface. However, inadequate (0.5 M diethanolamine) and outrageous (1.5 M diethanolamine) concentration of the functionalization agent impeded adequate CO₂ adsorption. The presence of larger amine molecules at higher concentration may have affected the WTAC surface area thereby reducing the adsorption activity area. On the contrary, inadequate availability of the amine molecules on the WTAC surface to increase the vacant active sites may not had measured up the available and numerous CO₂ adsorbate molecules available for adsorption. The increase in CO₂ adsorption observed with 1.0 MWTAC adsorbent was attributed to even distribution of the molecules of the functionalization agent on the adsorbent surface in a proportionate manner. The amount of CO₂ adsorbed by these adsorbent was in this order 1.0 MWTAC > 1.5 MWTAC > 0.5

MWTAC > UWTAC. The clear distinction and better adsorption observed with amine modified adsorbent (MWTAC) was attributed to dual (chemical and physical) sorption through formation of bicarbonate and carbamate and, permeation of CO₂ molecules to the pores; unlike the UWTAC adsorption that was probably physically based [3,18].

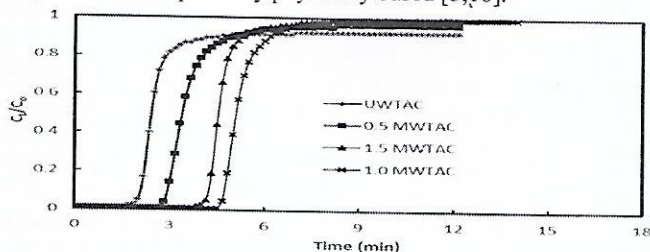


Fig. 4 Effect of functionalization agent (diethanolamine) concentration on breakthrough curves at 10 % CO₂ feed concentration (balance of N₂), 90 mL/min feed flow rate, 3 g adsorbent dosage, 1.0 M MWTAC particle sizes of 1-2 mm, adsorption column temperature of 30 °C.

Effect of the CO₂ feed concentration on the breakthrough curves

The concentration of CO₂ in the feed determined the available flow of the adsorbate molecules that interacted with the active site on the fixed adsorbent surface. The level of electrostatic attraction between the active sites of the adsorbent surface and the adsorbate molecules informed the suitability of the CO₂ feed concentration adequate for adsorption. The effect of the initial CO₂ feed concentration variation on the breakthrough point is presented in Fig. 5. The Fig. 5 revealed that 10 % CO₂ concentration in the feed at 90 mL/min was most suitable for the adsorption study as it recorded an adsorption capacity of 53.62 mg/g and 900 s breakthrough time. This was evident in the longer breakthrough curves and higher adsorption capacity that resulted. However, further increase in the initial CO₂ feed concentration (15 to 20 %) resulted in the reduction of the MWTAC adsorption capacity (50.70 and 46.84 mg/g at 580 and 530 s, respectively). This may be attributed to overwhelming and poor attraction of the adsorbent active sites when larger numerous CO₂ molecules were available for uptake.

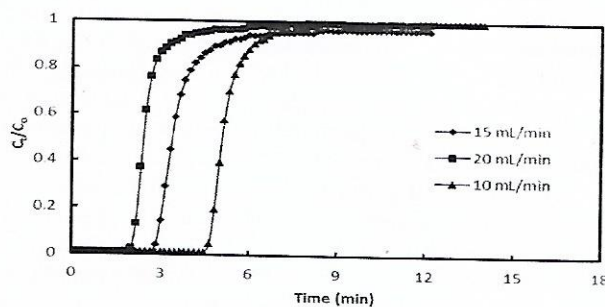


Fig. 5 Effect of CO₂ feed concentration on breakthrough curves at 30 °C adsorption column temperature, 90 mL/min feed flow rate, 3 g adsorbent dosage, 1.0 M MWTAC particle sizes of 1-2 mm.

IV. CONCLUSION

Modification of mesoporous waste tea activated carbon with diethanolamine was successfully carried out and used for the adsorption of carbon dioxide from gaseous mixture (CO₂ and N₂). The 1.0 M MWTAC adsorbent removed CO₂ from the fluid in both physical and chemical processes (physisorptive). The optimum conditions for adsorbing CO₂ were at adsorption column temperature of 30 °C, 10 % CO₂ feed concentration, 90 mL/min influent fluid flow rate, 3 g adsorbent (1-2 mm particle sizes) dosage.

REFERENCES

- [1] Fisher II, J.C., Tanthana, J., Chuang, S.S.C. 2009. Oxide-Supported tetraethylpentane for CO₂ capture. *Environmental Progress & Sustainable Energy*, 28(4), 589-598.
- [2] Labreche, Y., Lively, R.P., Rezaci, F., Chen, G., Jones, C.W., Koros, W.J. 2013. Post-spinning infusion of poly(ethyleneimine) into polymer/silica hollow fiber sorbents for carbon dioxide capture. *Chemical Engineering Journal*, 221, 166-175.
- [3] Sharma, P., Seong, J-K., Jung, Y-H., Choi, S-H., Park, S-D., Yoon, Y., Beak, Il-H. 2012. Amine modified and pelletized mesoporous materials: Synthesis, textural-mechanical characterization and application in adsorptive separation of carbon dioxide, *Powder Technology*, 219, 86-98
- [4] Su, F., Lu, C., Kuo, S.-C., Zeng, W. 2010. Adsorption of CO₂ on Amine-Functionalized Y-Type Zeolites. *Energy and Fuels*, 24, 1441-1448.
- [5] Shafeeyan, M.S., Daud, W.M.A.W., Houshmand, A., Shamiri, A. 2010. A review on surface modification of activated carbon for carbon dioxide adsorption. *Journal of Analytical and Applied Pyrolysis*, 89(2), 143-151.
- [6] Chatti, R., Bansawal, A.K., Thote, J.A., Kumar, V., Jadhav, P., Lokhande, S.K., Biniwale, R.B., Labhsetwar, N.K., Rayalu, S.S. 2009. Amine loaded zeolites for carbon dioxide capture Amine loading and adsorption studies. *Microporous and Mesoporous Materials*, 121, 84-89.
- [7] Bali, S., Chen, T.T., Chaikittisilp, W., Jones, C.W. 2013. Oxidative stability of amino polymer-alumina hybrid adsorbents for carbon dioxide capture. *Energy and Fuels*, 27, 1547-1554.
- [8] Ma, L., Bai, M.R., Hu, G., Chen, R., Hu, X., Dai, W., Dacosta, H.F.M., Fan, M. 2013. Capturing CO₂ with amine-impregnated titanium oxides. *Energy and Fuels*, 27, 5433-5439.
- [9] Stevens, L., Williams, K., Han, W.Y., Drage, T., Snape, C., Wood, J., Wang, J. 2013. Preparation and CO₂ adsorption of diamine modified montmorillonite via exfoliation grafting route. *Chemical Engineering Journal*, 215-216, 699-708.
- [10] Auta, M., Hameed, B.H. 2011a. Optimized waste tea activated carbon for adsorption of Methylene Blue and Acid Blue 29 dyes using response surface methodology. *Chemical Engineering Journal*, 175, 233-243.
- [11] Auta, M., Hameed, B.H. 2014. Adsorption of carbon dioxide by diethanolamine activated alumina beads in a fixed bed. *Chemical Engineering Journal*, 253, 350-355
- [12] Auta, M., Hameed, B.H. 2011b. Preparation of waste tea activated carbon using potassium acetate as an activating agent for adsorption of Acid Blue 25 dye. *Chemical Engineering Journal*, 171(2), 502-509.
- [13] Pevida, C., Drage, T.C., Snape, C.E. 2008. Silica-templated melamine-formaldehyde resin derived adsorbents for CO₂ capture. *Carbon*, 46(11), 1464-1474.
- [14] Plaza, M.G., Pevida, C., Arenillas, A., Rubiera, F., Pis, J.J. 2007. CO₂ capture by adsorption with nitrogen enriched carbons. *Fuel*, 86(14), 2204-2212.
- [15] Li, M. 2011. Dynamics of CO₂ adsorption on sodium oxide promoted alumina in a packed-bed reactor. *Chemical Engineering Science*, 66(23), 5938-5944.
- [16] García, S., Gil, M.V., Martín, C.F., Pis, J.J., Rubiera, F., Pevida, C. 2011. Breakthrough adsorption study of a commercial activated carbon for pre-combustion CO₂ capture. *Chemical Engineering Journal*, 171(2), 549-556
- [17] Tan, I.A.W., Ahmad, A.L., Hameed, B.H. 2008. Adsorption of basic dye using activated carbon prepared from oil palm shell: batch and fixed bed studies. *Desalination*, 225(1-3), 13-28.
- [18] Lee, C.S., Ong, Y.L., Aroua, M.K., Daud, W.M.A.W. 2013. Impregnation of palm shell-based activated carbon with sterically hindered amines for CO₂ adsorption. *Chemical Engineering Journal*, 219, 558-564.