

Journal Pre-proofs

Review article

Nanofluids and their application in carbon fibre reinforced plastics: A review of properties, preparation, and usage

Sunday A. Lawal, Rasaq O. Medupin, Kelvin O. Yoro, Uzoma G. Okoro, Oyewole Adedipe, Joseph Abutu, Jimoh O. Tijani, Abdulkareem S. Abdulkareem, Kingsley Ukoba, Mohammed B. Ndaliman, Patrick T. Sekoai, Tien C. Jen

PII: S1878-5352(23)00370-2
DOI: <https://doi.org/10.1016/j.arabjc.2023.104908>
Reference: ARABJC 104908


To appear in: *Arabian Journal of Chemistry*

Received Date: 19 November 2022
Revised Date: 8 April 2023
Accepted Date: 9 April 2023

Please cite this article as: S.A. Lawal, R.O. Medupin, K.O. Yoro, U.G. Okoro, O. Adedipe, J. Abutu, J.O. Tijani, A.S. Abdulkareem, K. Ukoba, M.B. Ndaliman, P.T. Sekoai, T.C. Jen, Nanofluids and their application in carbon fibre reinforced plastics: A review of properties, preparation, and usage, *Arabian Journal of Chemistry* (2023), doi: <https://doi.org/10.1016/j.arabjc.2023.104908>

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2023 The Author(s). Published by Elsevier B.V. on behalf of King Saud University.

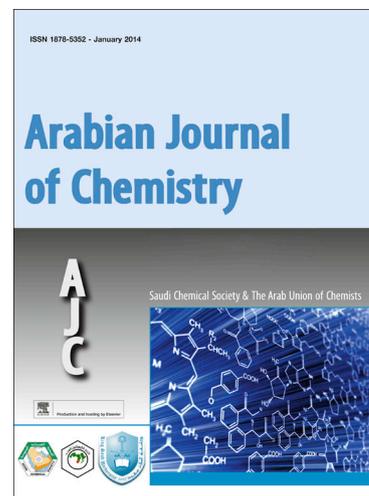

Nanofluids and their application in carbon fibre reinforced plastics: A review of properties, preparation, and usage

Sunday A. Lawal^a, Rasaan O. Medupin^b, Kelvin O. Yoro^{*, c}, Uzoma G. Okoro^a, Oyewole Adedipe^a, Joseph Abutu^d, Jimoh O. Tijani^e, Abdulkareem S. Abdulkareem^e, Kingsley Ukoba^f, Mohammed B. Ndaliman^a, Patrick T. Sekoai^h, Tien C. Jen^f,

^aDepartment of Mechanical Engineering, Federal University of Technology, Minna, Nigeria

^bDepartment of Materials and Metallurgical Engineering, Federal University of Technology, Owerri, Nigeria

^cEnergy Technologies Area, Lawrence Berkeley National Laboratory, 1 Cyclotron Road, Berkeley, CA, 94720, United States.

^dDepartment of Mechanical Engineering, Taraba State University, Jalingo, Nigeria

^eDepartment of Chemistry, Federal University of Technology Minna, Nigeria

^fDepartment of Chemical Engineering, Federal University of Technology, Minna, Nigeria

^gDepartment of Mechanical Sciences, University of Johannesburg, Auckland Park, South Africa.

^hBiorefinery Industry Development Facility, Council for Scientific and Industrial Research, Durban 4041, South Africa

*Corresponding author email: kelvin.yoroo@gmail.com

Abstract

The renewed call for the replacement of conventional materials with carbon fibre reinforced plastics (CFRPs) in many high-performance applications is responsible for the current wave of research on minimum quantity lubrication (MQL) strategy in machining. Due to their competitive advantages over conventional materials, polymer matrix composites (PMCs) materials have become advanced and therefore deserve more attention, especially in the field of machining. Although most manufacturing methods require less machining, precision machining like milling and drilling call for more research inputs. For this purpose, this review article assesses various aspects of nanofluid preparation and its application in CFRPs. Recent peer-reviewed literature on nanofluids with a focus on properties, preparation, and application (including respective methodologies) is analyzed to contribute to the growing database in this field for future research. This review article also shows that cutting temperature and cutting force remain the key determinants of surface finish while tool wear constitutes a major parameter that machining scientists would like to keep under full control by the use of

appropriate cutting fluid. The question of the quality of nanofluids which is scarcely discussed in the literature is also raised while advocating for more works to unravel it. Furthermore, this review article sheds more light on the machining operations of carbon fiber-reinforced plastics using nanoparticle-laden fluids for a safe and sustainable machining experience. Finally, this review assesses the possibility of achieving excellent CFRP processing by using a sustainable approach to filling the gaps that exist in form of wasted cutting liquids, environmental pollution, and exposure of operators to health hazards.

Keywords: Nanofluids, Machining, Manufacturing, Minimum quantity lubrication, Carbon fibre reinforced polymer

1. Introduction

Researchers have channeled a tremendous amount of energy toward the creation of a safe, sustainable, and effective manufacturing environment; hence the need to pay attention to machining. Cutting fluids are important materials that could be used to achieve optimal surface finishes. Machinists simply take advantage of an abundant supply of coolants to achieve speedy cooling and lubricating effect as well as quick removal of chips. However, the need for a high volume of cutting fluids and additional peripheral equipment becomes a huge worry (Madanchi et al., 2019).

Significant effort has been made by scientists in recent times to explore nanofluids and their potential lubricating potential. Singh et al. (2017) defined lubrication as the process by which wear of either or both the surfaces or parts in relative movement to each other is reduced by the abrupt and deliberate introduction of lubricants between the surfaces to remove the pressure generated during the opposing movement. The main objectives of the lubrication were to reduce wear and tear, as well as heat generated due to friction, thereby protecting surfaces against corrosion. Bio-lubricants have been identified as an excellent substitute for synthetic lubricants in the machining of heat-resistive superalloys because they offer the most sustainable mode of machining for both micro and nano-fluids (Sen et al., 2020; Venkatesh et al., 2018). However, of all the lubrication approaches, nano-lubrication has emerged as one of the most sustainable, renewable, and energy-efficient lubrication strategies in machining processes (Zadafiya et al., 2021; Huang et al., 2017; Pal et al., 2021). Different variables, including production time, cost, and energy consumption, are minimized by the use of appropriate cutting fluids (Agapiou, 2018).

While machining quality is said to depend on the speed of cutting, feed rate, properties of materials being cut, and the choice of appropriate cutting fluids also affects the quality of finished surfaces (Rapeti et al., 2016). According to Venkatesh et al (Venkatesh et al., 2018) cutting fluids are effective coolants meant to convey heat away from the tool/workpiece interface during machining. Common coolants (water, mineral oil, synthetic oil, vegetable oil, etc) are used as base oils and perform the same functions. However, they are ineffective in their raw state because of chemical imbalances and could facilitate the corrosion process (Pimenov et a., 2021). Therefore, nanoparticles-laden base oils are currently investigated to address issues around quick heat removal from the interface between tool and workpiece by leveraging the large surface areas of nanoparticles (NPs).

Nano-cutting fluids are principally fluids containing lower volume concentrations of NPs which are generally used during cutting operations. Pimenov et al (Pimenov et a., 2021) presented findings on improvements in machining activities achievable with NPs being homogeneously dispersed in base fluids. Given the non-biodegradable nature of most of the conventional cutting fluids currently in use, as well as health-related issues like skin and lung diseases, MQL has emerged as a more environment-friendly option (Padmini et al., 2019). Lubrication failure at higher metal removal and environmental pollution are common problems associated with most conventional coolants. Flood cooling is common with this type of machining. Hence, the machining environment is usually flooded with hazardous chemicals (Ma et al., 2022). This does not align with the SDGs guidelines on responsible production and consumption. In addition, the vibration and noise that often result from certain machinery underscore the need to find suitable alternatives that could help address these challenges. To proffer a solution to these problems, Jia et al. (2020) suggested the use of viscoelastic damping materials for vibratory noise reduction owing to their low densities, high strengths, and high elastic moduli. Furthermore, Feito et al.(2019) identified local delamination as the most challenging impairment associated with machining CFRPs. Zadafiya et al. (2021) reported an approximately 58% reduction in tool wear rate by using a nanofluid of 1% volume concentration in contrast to traditional and dry machining. Other indicators that increase because of the increment in the concentration of NPs include fluid viscosity, thermal conductivity, and density. The challenges encountered with conventional materials in all applications have triggered intense research for the development of both natural and synthetic fiber-reinforced polymer (nano)composite materials to address the aforementioned agelong issues(Bokobza, 2019; Feldman, 2017; Pozegic et al., 2016; Mensah et al., 2015; Kumar et al.,

2021; Veeman et al., 2021; Medupin et al., 2017; Scholz et al., 2011; Guo and Zhang, 2021; Oleiwi et al., 2022; Sathyanarayana and Hubner, 2013; Salah et al., 2019; Zwawi, 2021; Benzait and Trabzon, 2018; Guo et al., 2020; Sun et al., 2021; Wang et al., 2014; Abdalla et al., 2010; Lin et al., 2020; Zaaba and Ismail, 2019; Arumugam and Ju, 2021; Jawahar et al., 2020; Medupin et al., 2019). Some of these polymer nanocomposites are applied in such areas which would require resizing to the design specifications, hence the need for machining with other conventional materials often arises (Mohammed et al., 2015; Jose and Athikalam, 2020).

Furthermore, maintaining the chemical stability of nano-cutting fluids is a huge challenge among researchers in the field (Goindi and Sarkar, 2017). Zadafiya et al. (2021) investigate an effective lubrication system that meets sustainability requirements without trading off manufacturing efficiency and product quality. In another study, Wickramasinghe et al. (2021) opined that most vegetable oils have stability issues resulting in poor cooling performance during machining operations. Similarly, Kumar et al. (2023) recently reported that the addition of nanoparticles boosts the lubricating performance of pure oils; adding that the sustainability of machining operations is greatly improved by the reduction of cutting forces, cutting temperature, tool wear, and surface roughness. Despite the recent clamor for a paradigm shift from conventional materials to composites (polymer nanocomposites), there is still a dearth of scientific reports on improving manufacturing activities in polymer structures sectors like housing, and automobile manufacturing.

In this study, we seek to explore insightful information on nano-based cutting fluids for a wide range of applications. We examine the possibility of using non-destructive nano-coolants loaded with NPs in machining operations. Finally, this review explores pioneer and recent research in the field to update stakeholders in the field on machining operations of carbon fiber-reinforced plastics using nanoparticles-laden fluids for safe and sustainable machining experience.

2. Preparation of nano-based cutting fluids

The production economy of nano-coolants plays an important role in determining their acceptability amongst stakeholders in the field (Shahnazar et al., 2016). So far, one-step and two-step methods are the most widely used techniques for the preparation of nano-coolants (Usha et al., 2019). Between these two methods, recent research findings reveal that the two-step method is unique and widely accepted because of its cost competitiveness, as well as its

adaptability for the wide-ranging production of nano-coolants (Pownraj and Valan Arasu, 2020). The two-step preparation method involves the dispersion of NPs in two rounds of processes. The NPs are then homogeneously distributed in the base oil to form nano-lubricant/coolant. The choice of oils used in this method is often based on cost, good lubrication capacity as well as biodegradability of the resulting wastes (Ni et al., 2021; Makhdoum et al., 2023). The procedure proposed for the synthesis of NPs in this review is summarized in Fig. 1.

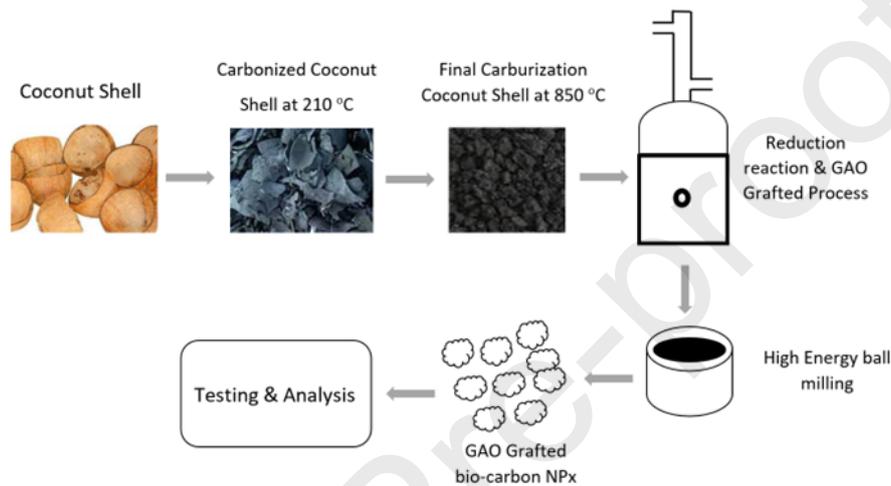


Fig. 1: Synthesis of GAO-grafted coconut shell carbon nanoparticles. Adapted and modified from (Pownraj and Valan Arasu, 2020)

Table 1: Summary of nano-cutting fluid preparation in recent literature

Reference	Nanoparticles	Base oil type	Preparation Technique	Method
(Singh et al., 2019)	nTiO ₂	Euphorbia lathyrus oil	Ultrasonication was utilized to achieve to mix Euphorbia lathyrus oil and the NPs in varying percentages and blended with ultrasonic for a period of 1 h.	One-step
(Sen et al., 2020)	nSiO ₂	Pure palm oil	Between 0.5 and 1.5%, nSiO ₂ was added to base oil, and afterward ultrasonication process was carried out to achieve uniform dispersion of the NPs in the presence of surfactant to minimize the surface tension and improve silica/pure palm oil nanosuspension.	Two-step
(Pal et al., 2021)	nAl ₂ O ₃	Vegetable oil	A fixed amount of nAl ₂ O ₃ plus sunflower vegetable oil was subjected to magnetic stirring for ½ h and then ultrasonicated for ½ h.	Two-step
(Padmini et al., 2019)	nMoS ₂	Coconut oil Sesame oil Canola oil	Pre-measured quantity of nMoS ₂ was added to 100 ml of vegetable oil slowly while manually mixing to obtain a uniform suspension. The nanosuspensions were subjected to	Two-step

			thorough sonication for 1 h and afterward placed in a bath-type ultra sonicator for another 1 h	
(Pownraj and Valan Arasu, 2020)	coconut shell carbon	SAE 20 W40	Activated carbon of coconut shell was dispersed in the host oil using a magnetic stirrer for 2 h and afterward final dispersion using a homogenizer at $\frac{3}{4}$ h 10,000 rpm	Two-step
(Usha and Srinizasa, 2019; Ni et al., 2021)	Soft particle carbon Fe_3O_4 , Al_2O_3	Sesame oil De-ionized water	Introduction of non-toxic surfactants into sesame oil. The weight of both PEG and SDBS equal that of NPs, hence reduction of surface tension of nanofluids and mixture stability. Magnetic stirring then took place for $\frac{1}{2}$ h, followed closely by ultrasonication for $\frac{3}{4}$ h in the second step.	Two-step
(Gaurav et al., 2020)	nMoS_2	LRT 30 oil (mineral-based) Jojoba oil (vegetable-based)	Dispersion of different concentrations by weight of nMoS_2 (0.1%, 0.5%, and 0.9%) in LRT 30 oil and jojoba oil using ultrasonic microprocessor-based vibrator generating pulses of 40 kHz at 100 W	Two-step
(Mirzaasadi et al., 2021; Boyou et al., 2019)	nSiO_2	Water-based drilling fluid	nSiO_2 was dispersed in two steps, pre- and post-hot rolling at ambient and much higher temperatures (121.11 & 148.88 °C) respectively.	Two-step
(Baskaran et al., 2022)	nMoS_2	Used cooking oil	Ball milling of oil and nMoS_2 for 12 h to allow the nanosuspension to remain homogeneously spaced and distributed.	One-step
(Aramendiz and Imqam, 2019)	nSiO_2 nano-graphene	Water-based drilling fluid	300 ml of deionized water was poured into the flask and the NPs were slowly added using a magnetic stirrer. This was followed by an ultrasonication step at 40 kHz and 185W for 1 h to promote a better dispersion of the NPs.	Two-step
(Sharma et al., 2016)	nTiO_2 nAl_2O_3 nSiO_2	vegetable oil-water emulsion	Continuously ultrasonication for 6 h, followed by magnetic stirring to break down nanoparticle aggregates in the base oil.	Two-step
(Dey et al., 2021)	nCeO_2	diesel-palm biodiesel blends	A combination of mechanical homogenizer and ultrasonicator and surfactants Span 80, and Tween 80 were used to enhance the stability of the NPs.	Two-step
(Bhaumik et al., 2020)	Graphene and zinc oxide	Glycerol	The mixing of the solution (0.1 wt % graphene oxide and 0.08 wt % zinc oxide plus glycerol followed the common route to magnetic stirring and probe sonication for $\frac{3}{4}$ h intermittently. The solution was then homogenized using a homogenizer.	Two-step
(Virdi et al., 2020)	nAl_2O_3	Sunflower oil Rice bran vegetable oil	10 min of magnetic stirring and $\frac{1}{2}$ h of ultrasonication achieved the desired nanosuspension.	Two-step
(Borode et al., 2021)	Al_2O_3	Graphene nanoplatelet	Followed the procedure described by Virdi et al. (2021) but sonicated for $\frac{3}{4}$ h instead of $\frac{1}{2}$ h.	Two-step

As shown in Table 1, magnetic mixing and ultrasonic combination were necessary to ensure a uniform distribution of NPs in the base oil. Surfactants were also often used to achieve stability of NPs in the nanosuspension. Of all the reviewed literature summarized in Table 1, only 12% of the authors adopted the one-step methodology for preparing nano-cutting fluids. While magnetic stirring can also lead to significant uniform distribution of microparticles (MPs) in the base oil, it could be grossly inadequate in the case of NPs (Okokpujie and Tartibu, 2020). Therefore, the two-step method of nano-fluid preparation is more favored for the achievement of stable nanosuspension for machining operations.

As shown in Table 1, various types of NPs including, metal oxides and other non-metallic materials can be used as nano reinforcements, that could be incorporated into a wide range of base fluids (Sofiah et al., 2021; Urmi et al., 2021). The preparation method is vital to the stability of nanofluid systems, which is needed for the improvement of heat transfer. Therefore, any procedure that would impact the dispersibility of NPs positively, will also support the durability and chemical stability of nanofluids. Some researchers have argued that due to the Brownian motion phenomenon, reduced nano additives favor the stability of nanofluid systems (Kaggwa and Carson, 2019), while others argue that nanofluid chemistry and NP types are more significant to the creation of a steady nanofluid ((Li et al., 2022; Ouabouch et al., 2021). However, in this review, it was discovered that some nanofluids can attain equilibrium without any stabilizers, but could agglomerate up to 250% over s time due to high surface energy). Consequently, we agree that the stability of nanofluid systems is strongly connected to the method of preparation. One-step and two-step preparation methods of nanofluid are schematically described in Fig. 2.

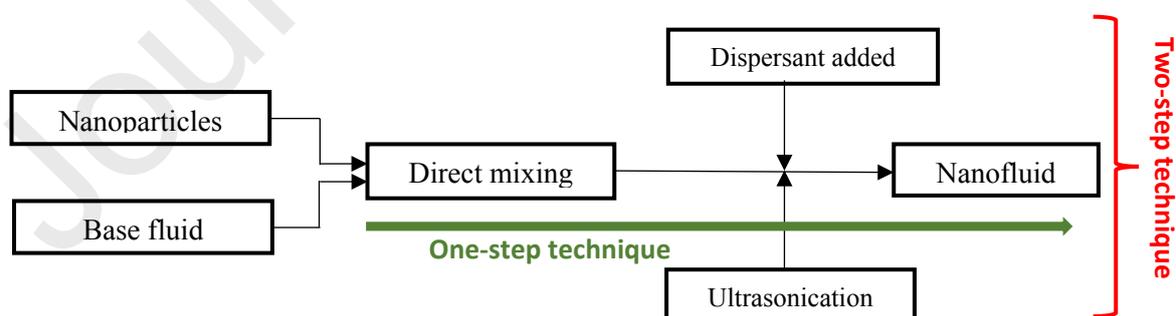


Fig. 2: One-step and two-step techniques of nanofluids preparation. Adapted and modified from Mirzaadi et al. (2021)

According to Mirzaadi et al. (2021), the one-step approach involves synthesizing the NPs and producing the nanofluids in one direct process as depicted in Fig 2. The major advantage of the one-step technique is that the processes occur concurrently. Hence, mitigating issues arising from drying, suspension, and transportation of NPs after synthesis. In addition, the one-step technique significantly reduces the chances of nano additive aggregation (Ali and Salam, 2019). Ali and Salam (2019) further corroborated the findings in the early work by Zhu et al. (Zhu et al., 2004) by alluding to their assertion that pure and uniform NPs are produced by this method. Apart from the challenge of the cost associated with the one-step method, the main drawback is that the residual reactants which help to stabilize the NPs are often left in the nanofluids.

In the two-step method, NPs are synthesized in one stage and dispersed in the base fluid in the second stage through some mechanical processes like mechanical stirring, ultrasonication, and high-pressure homogenization as shown in Fig 2. It is described as the most cost-effective method for the large-scale preparation of nanofluids. Rapid aggregation of NPs is the main limitation of this method, which is why the formation of surfactants is popular with the two-step method. According to Zhu et al. (2021), the environmental impact of this method is far lesser than the one-step technique. The difference between the two techniques is illustrated in Fig. 2 where ultrasonication and the addition of dispersants are peculiar only to the two-step technique.

3. Pure and minimum quantity lubrication of nanofluids

Minimum quantity lubrication (MQL) was introduced to address challenges associated with orthodox lubrication techniques where high-quantity flood coolant is used during the machining process. This conventional method is plagued with many limitations including the unrestrained spillage of coolant, wet chips with its resulting adverse effect on the cutting tool, allergies to the skin of operators, and disposal issues (Kumar et al., 2023). MQL has a strong influence on the cutting temperature over a wide range of speeds in a machining process, thereby lowering the wear rate of the cutting tool compared to entirely dry machining (Krolczyk et al., 2019). However, lower thermal conductivity cutting fluid, even with the help of MQL cannot fully establish green machining. Recent research findings show that the heat transfer of conventional fluids like oil can be significantly improved by the addition of NPs (Alaboodi et al., 2020), although intensive cooling of tools and chips during machining can be achieved by cryogenic cooling (Bordin et al., 2017; Bermingham et al., 2011).

Nanoparticles are specifically introduced into conventional cutting fluids to enhance the machining process. In a related study, Wickramasinghe et al. (2020) explored the benefits that NPs bring to machining operations. The researchers concluded that NPs are an integral part of effective machining operations. On the other hand, other researchers have reported incessant incidence of scratches and marks on the surfaces of machined parts while using NP-laden cutting fluids for improved thermal stability (Mao et al., 2014; Tran Minh Duc, 2019).

According to Bhardwaj (2020), the use of nanofluids in machining operations was discovered due to the need to control the intense heat generated by microchips at the tool/workpiece interface. Although heat removal is a great achievement in most machining processes, more is needed to understand the remote causes of the defects, as well as the required concentration of nano-additives that will be enough to not only facilitate heat removal but also enhance the surface finish of machined components and conserve cutting fluids.

Virdi et al. (2020) have reported how nanofluids MQL (nMQL) can produce better machining performance of metallic components concerning coefficient of friction, grinding energy, and surface roughness as against pure MQL. Cui et al. (2021) described MQL as an upbeat method to resolve lubrication and cooling challenges for hard-to-machine workpieces, by introducing bio-lubricant with a 10–100 mL/h flow rate into the interface between the workpiece and cutting tool through high-pressure airflow. However, the unregulated disposal of coolants still poses a great threat to the environment. Table 2 presents a summary of selected studies on pure and nMQL for sustainable machining.

Table 2: Summary of findings on pure and nanofluid MQL

Reference	Method Deployed	Focus of Study	Machining output measured	Findings	Sustainability perspective	Operations
(Huang et al., 2017)	Nano-MQL	Analysis of the performance of various coolant-lubricant environments.	Surface roughness Drilling force Tool wear Drilling temperature	Drilling force reduced by up to 40% and 82% for pure and nano MQL respectively	Reduction of environmental pollution as well as processing cost of cutting fluid.	Drilling
(Padmini et al., 2019)	Nano-MQL	Performance of vegetable oil-based nano-cutting fluids	Cutting forces Cutting temperatures Tool wear surface roughness	Vegetable oil-based nano-cutting fluids have the potential to improve machining performance	Eco-friendly and operator-friendly machining environment.	Turning
(Gaurav et al., 2020)	Nano-MQL	Investigation on jojoba base oil	Cutting force Tool wear Surface finish	Unreinforced and nMoS ₂ , reinforced jojoba oil proved	Clean, healthy, and near-dry working environment, the	Turning

		with and without nMoS2		sustainable as a machining alternative.	MQL with jojoba oil is 27% economic compared to commercial mineral oil.	
(Viridi et al., 2020)	Nano- MQL	Investigation of Inconel-718 grinding	Grinding energy Surface finish G-ratio Grinding force	Better machining performance was achievable due to the high viscosity of sunflower oil and the presence of high saturated fatty acids.	Economic and ecological issues addressed with nano-MQL	Grinding
(Khan et al., 2009)	Pure MQL	Influence of MQL vegetable oil-based cutting fluid on machining	Chip formation modes Tool wear Surface finish Cutting temperature	MQL systems reduce the average chip-tool interface temperature possible compared to wet machining	Reduction in lubricant consumption	Turning
(Sakthi et al., 2021)	Nano- MQL	Study of health hazards associated with traditional machining method.	Metal removal rate	50% coolant reduction during machining and also.	Reduce environmental impact	Turning

MQL offers unique benefits in terms of cost (owing to reduced coolant usage and large disposal saving), as well as ecological and human safety. Several studies have reported MQL in the past (Maruda et al., 2015; Dhar et al. 2006). .. In another study, Tasdelen et al. (Tasdelen et al., 2008) reported that controlled tool wear and shorter chip lengths were attainable with MQL than conventional metal-working fluids (MWFs) in hardened steel drilling. In a separate study, another group of researchers compared the use of MQL with traditional MWFs in AISI 9310 turning in terms of tool life and surface quality (Khan et al., 2009). Both teams concluded that MQL presented better results than the traditional MWFs. However, Zhang et al. (2015) identified surface burning as a major drawback in the MQL grinding of a nickel alloy. As described in the preceding sections of this review study, pure MQL is fast giving way to nMQL because of the latter's faster and more effective heat removal advantage. The reports point to improved machining performance as all the outputs measured (cutting force, cutting temperature, tool wear, and surface roughness) reduced considerably, compared to conventional machining (Sabarinathan et al., 2020). It can also be deduced from Table 2 that both methods are human and environment-friendly and in agreement with the work of Agapiou et al. (2018).

Table 3 shows the growing acceptability of vegetable oil as a viable replacement for petroleum-based coolants, as well as lends credence to the fact that green machining is one of the most important evolving industrial study areas in recent times.

Table 3: Literature review on various aspects of nano-cutting fluids

Reference	Nanoparticles type	Component	Base oil	Focus of study	Findings	Operation (Test)
(Madanchi et al., 2019)	-	metals	Vegetable oil	Cutting fluid strategies on environmentally conscious machining systems	The supply strategy type of cutting fluid has a significant impact	varied
(Pal. Et al., 2021)	Al ₂ O ₃	AISI 321 stainless steel	Vegetable oil	Assessment of coolant-lubricant environments concerning drilling parameters.	MQL drilling with Al ₂ O ₃ /vegetable-oil-based cutting fluid accomplished better performance as compared to drilling with other techniques. Cost reduction in the machining of steel gears with CNO water-based or oil-cutting fluids.	Drilling
(Agapiou, 2018)	Carbon onion	Steel gear	MWF	Performance evaluation of carbon nano-onions cutting fluids.	Coconut oil-based nanographene cutting fluids are effective in causing a reduction in cutting forces & temperatures, tool wear, and surface roughness.	varied
(Ppadmini et al., 2019)	nGraphene	AISI 1040 steel	coconut oil and canola oil	Assessment of vegetable oil-based nano-cutting fluids	1% silica-deposited palm oil medium performs better concerning all machining responses.	Turning
(Sun et al., 2021)	Nano silica	Inconel 690	pure palm oil	Performance of minimum quantity nano-green lubricant in milling.	The significant parameters influencing cutting force are depth of cut, and feed rate followed by MQL flow rate.	Milling
(Usha and Srinivasa Rao, 2019)	Al ₂ O ₃	AISI 1045 steel	De-ionized water	Study of the optimal cutting force while turning AISI 1045 steel using nAl ₂ O ₃ particles.	Carbon nanofluid demonstrated the best results in broaching load, broaching vibration, and surface quality concerning other cutting fluids.	Turning
(Ni et al., 2021)	Fe ₃ O ₄ , Al ₂ O ₃ , Carbon	AISI 1045 steel	Sesame oil	Assessment of MQL broaching AISI 1045 steel with NPs reinforced sesame oil.	Jjoba oil, in pure and nano-fluidic conditions, proved a strong and	Broaching
(Gaurav et al., 2020)	nMoS ₂	Titanium alloy	Jjoba oil	Study on vegetable oil mixed with and without		Turning

				nMoS ₂ in hard machining with MQL.	sustainable replacement for commercial mineral oil for MQL turning.	
(Baskaran et al., 2022)	MoS ₂	SAE 1144 steel	waste cooking oil	Effect of the concentration of nMoS ₂ -laden waste cooking oil coolant in cutting force reduction.	nMoS ₂ enriched waste cooking oil-based wet machining reduced the cutting force by 27.53% more than the green machining method.	varied
(Dey et al., 2021)	CeO ₂	metals	palm biodiesel	Combustion-performance-emission characteristics of cerium oxide (CeO ₂)	Adding nCeO ₂ to palm biodiesel blends improves the thermal efficiency of the brake and reduces energy consumption in practice.	varied
(Virdi et al., 2020)	0.5% Al ₂ O ₃	IN718 alloy	Vegetable oils	Investigating forces, surface roughness, grinding energy, and -ratio under MQL, flood	Significant improvement in grinding performance of Inconel-718 alloy with respect to G-Ratio, Grinding Energy, and Surface Roughness.	Grinding
(Bhardwaj, 2020)	Al and Cu	Steel ball	Toluene	Synthesis of 0.025 vol% Al and Cu-based nanofluids by two-step technique.	Nanoparticles with lower density, good conducting properties, and finer particle size positively impact dispersion stability in most of the conventional heat transfer fluids.	Milling
(Cui et al., 2021)	α -Al ₂ O ₃	Al ₂ O ₃ /TiC micro-composite ceramic	Vegetable oil	Green cutting performance for the bio-inspired microstructure on Al ₂ O ₃ /TiC composite ceramic surface.	Higher transport speed amounted to more adequate lubrication and lower cutting load.	varied
(Sakthi et al., 2021)	Al ₂ O ₃	magnesium alloy	Varied	Effect of nano additives on Mg alloy during turning operation with MQL	MRR which is influenced by cutting speed, constant feed, and depth of cut and nano additives saves 50% of coolant by the MQL system.	Turning
(Mahmoud et al., 2020)	Inert fibres	Unspecified	Water-Based Muds	Effect of anionic and fiber on cutting carrying capacity of polymeric suspensions.	The cutting carrying capacity of nanosuspensions was increased by increased anionicity owing to improved particle-particle	Drilling

(Bhaumik et al., 2020)	Graphene oxide, ZnO	EN21 workpiece	Glycerol	Replacement of non-biodegradable and safe commercial cutting fluids by glycerol-based lubricants.	Carbonaceous nanoparticles additive performed better in respect of machined surface quality.	Turning
(Patole et al., 2021)	MWCNTs	steel AISI 4340.	ethylene glycol	Effect of cutting conditions, and nano coolant on machining parameters.	Feed rate and depth of cut are two major input parameters that influence surface roughness and cutting force during machining.	Turning
(Elsheikh et al., 2021)	Al ₂ O ₃ and CuO	AISI 4340 alloy	Vegetable oil	nMQL technique for turning of AISI 4340 alloy.	CuO/oil nanofluid improved surface finish and tool wear compared with Al ₂ O ₃ /oil nanofluid.	Turning
(Haq et al., 2021)	unspecified	IN718	Vegetable oil	Machining improvement of face milling of Inconel 718 by using two different lubrication conditions.	Depth of cut is the most significant process parameter influencing SR, temperature, MRR, and power.	Milling
(Mahadi et al., 2017)	Boric Acid Powder	AISI 431 Steel	Palm kernel oil	Performance evaluation of boric acid powder reinforced palm kernel oil for machining.	Boric acid powder-aided lubricant machining outperformed conventional lubricant by 7.21%.	turning
(Ghatge et al., 2018)	TiN/Al ₂ O ₃ /Ti CN/TiN cutting insert	Duplex Stainless Steel	Coconut and neem oil	Non-biodegradable mineral oil is replaced with vegetable oil as cutting fluid.	Lower tool wear results in low cutting speed and high feed rate.	Turning

4. Factors influencing the performance and qualities of nano-cutting fluids

Having demonstrated the superiority of nano-cutting fluids over dry machining and machining with water-based coolant, it is pertinent to touch on the factors influencing the performance of the nanofluids to build a formidable foundation for future research. In this section, a brief review of these elements is done.

Bhardwaj (Bhardwaj, 2020) confirmed, and reported that viscosity is one of the most important factors affecting the dispersion of NPs and the equilibrium of nanosuspension systems. The researcher demonstrated that viscosity increases with a lower density of Al₂O₃ NPs than with CuO-dispersed nanofluids. This could be attributed to the role smaller particle size plays in the thermal conductivity and stability of nanofluids (Ouabouch et al., 2021). The shape of NPs is

also said to affect the stability and thermal conductivity of nanofluids. Particles with cylindrical morphologies have a higher thermal conductivity than nanofluids with spherical particles. In an investigation of the influence of aspect ratio on thermal conductivity and viscosity of nanofluids, Ouabouch et al. (Ouabouch et al., 2021) reported that fibrous $n\text{Al}_2\text{O}_3$ exhibited a greater improvement in thermal conductivity and viscosity than spherical $n\text{Al}_2\text{O}_3$ nanofluids, which could be attributed to the larger surface area common with cylindrical-shaped particles.

The pH values of nanofluids which play an important role in the corrosion of the interface between the tool and workpiece are another factor to consider in formulating nanofluids. This is because of its impact on thermal conductivity and viscosity as well as particle clustering and stability of nanofluids. Fuskele and Sarviya (Fuskele and Sarviya, 2018) presented a close relationship between the stability and electrokinetic properties of nanofluids. researchers concluded that pH control is vital to achieving stability in nanofluids. Another group of researchers further confirmed that nanosuspension enjoys more stability when the pH is further away from its isoelectric point (IEP), where the surface charge of the nanoparticles and the values of the zeta potential is zero (Sharma and Gupta, 2016). The zeta potential typifies the voltage between the surface of the nanoparticles and the adjacent stationary layer of the base fluid (Sezer et al., 2019). As a result of these findings from previous research, we submit in this review that, the pH value of nanofluids is better maintained around the neutral point to forestall possible dissolution of the nanoparticles with the alkaline and acid-triggered corrosion at the heat transfer interface (Gbadimi et al., 2011). In another investigation of the effect of pH on the stability of nanofluids, Sahooli and Sabbaghi (Sahooli and Sabbaghi, 2013) concluded that the best stability and enhancement of thermal conductivity of NPs-laden fluids is achievable only with the optimal pH of the nanosuspension. Borode et al. (Borode et al., 2021) compared the thermal conductivity, density, specific heat, and viscosity of graphene nanoplatelet (GNP) with alumina hybrid nanofluids at different mixing ratios. They observed that the addition of NPs into base fluids improves the cooling ability with less impact on viscosity.

Karmakar et al. (Karmakar et al., 2017) studied the quality and performance of bio-lubricants. They observed that the quality of any nanofluids depends on certain physical properties which include viscosity index, flash point, cloud point, and thermal stability of the nanofluids. Other properties are oxidation stability, shear stability, iodine value as well as the density of the particles-laden base oil. The thermal stability of the nanofluids depends largely on their change in viscosity in response to temperature changes. According to Che (Che, 2014), higher viscosity

index and flash point nanofluids can withstand temperature fluctuations during machining operations. Therefore, regardless of the synthesis method, the thermal conductivity of all nanofluids gets enhanced by temperature (Ouabouch et al., 2021).

5. Machining of carbon fibre reinforced plastics: how conventional?

According to Uhlmann et al. (Uhlmann et al., 2021), CFRPs are widely used in manufacturing. The reinforcing fibers get randomly cut and deflected under the action of the cutting edge, thereby causing delamination in the form of fiber overhang and breakout at the machined edges. In recent times, CFRPs have become widely accepted in a range of applications including space engineering and military equipment manufacturing. Hence, they are envisaged to replace conventional materials owing to their low density, high strength and stiffness, good toughness, fatigue creep, wear and corrosion resistance, low friction coefficient, and good dimensional stability (Uhlmann et al., 2014). Although they are often fabricated to near net shapes by techniques like autoclave moulding, compression moulding, or filament winding, post-machining operation, such as turning, milling, or drilling is often needed to guarantee that the composite parts meet geometrical tolerance, surface quality, and other functional requirements (Che, 2014).

Turning is mostly used to achieve desired dimensional tolerance on cylindrical surfaces during machining operations. Most studies reported on CFRP composite machining prove that minimizing surface roughness is challenging (Rajasekaran et al., 2011). Various methods such as experimental measurements, theoretical modeling, and fuzzy logic algorithms, have been applied to understand the surface quality and dimensional properties of CFRP components during a turning process. Santhanakrishnan et al. (Santhanakrishnan et al., 1992) presented an experimental investigation involving cutting and tool performance in terms of force responses, tool wear, surface roughness, and chip formation using sintered carbides. Their findings revealed that sintered carbide tools can be used to generate homogenous surface finishes in CFRP machining if flank wear is carefully checked. In another study involving polycrystalline diamond turning, Palanikumar (Palanikumar, 2008) used Taguchi and response surface methodologies to reduce the surface roughness of CFRP. The good surface finish was linked to high cutting speeds, high depths of cut, and low feed rates which are in agreement with the findings of Lee (Lee, 2001) who experimentally determined that an increased feed rate favors increased surface roughness, while the depth of cut and cutting speed do not have any significant relationship with surface roughness.

In the manufacture of CFRP parts, milling is the most frequently used machining operation (Sarma et al., 2008). It is suited for the accurate machining of complex shapes on CFRP components as a corrective operation to produce well-defined and high-quality surfaces that often require the removal of excess material to control tolerances (Davim and Reis, 2005). The type of reinforcing agents used significantly impacts the machinability of CFRP composite and the possible delamination and burrs with uncut fibers that would occur due to the complexity of the interaction between the end mill and CFRP parts. Also, Kalla et al. (Kalla et al., 2010) suggested an exact forecast of thrust and axial cutting forces as a way of regulating the process parameters to circumvent delamination and reduce burr formation to the barest minimum. Sorrentino and Turchetta (Sorrentino and Turchetta, 2014), in a different study on the milling of CFRP parts, reported that the radial and tangential components of the cutting forces have a direct influence on the feed speed, depth of cut, and chip thickness. They concluded by proposing an experimental model for determining the cutting force components for CFRP milling.

Elgnemi et al. (Elgnemi et al., 2017; 2021) categorized CFRPs as hard-to-cut materials because of the abrasiveness of the reinforcing fillers and the resulting low transverse strength of composite layers leading to demarcation under machining forces. Hygroscopicity is reportedly a major limitation to the application of flood lubrication in the grinding of the composites. Researchers in this field are, therefore, left to decide in favor of MQL which has proven to be more sustainable and environment-friendly (but whose moisture could damage the structural integrity of CFRP), or dry machining which impacts both the operators and the environment negatively

6. Future of nano-based cutting fluids application in CFRPs

In spite of the reduced machining experience with CFRPs, Gao et al. (Gao et al., 2021) suggested that machining operations such as drilling and milling cannot be eliminated in polymer composite manufacturing, especially during the assembling of parts. Wet machining with scanning electron microscopy (SEM) images of various displaced fiber orientation angles, comparing the surface finishes obtained in a set of milling operations of CFRPs are presented in Fig. 3.

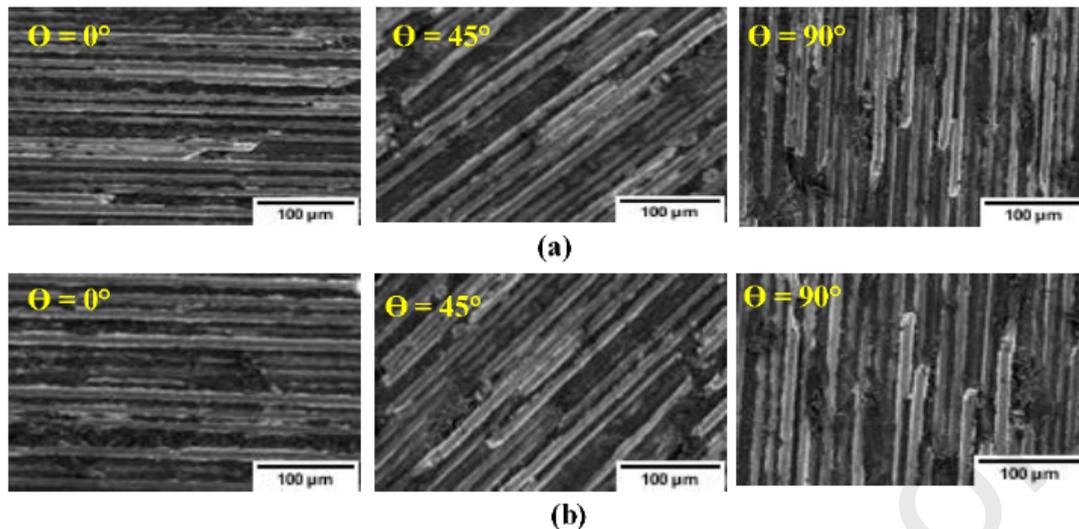


Fig. 3: SEM images of a machined surface obtained after milling operation (a) ACF vegetable oil conditions (b) dry (Adapted from Elgnemi et al., 2021)

The images illustrate surface damage of unidirectional CFRP laminates at 0° , 45° , and 90° displaced fiber orientation angles (FOAs). It can be observed that the surfaces for 45° and 90° orientation are more severely scratched than 0° . A careful comparison of the two sets of images shows that vegetable oil-conditioned milling (Fig. 3(a)) produces better surface finishes than unlubricated surfaces (Fig. 3(b)). Delamination percentage when cutting at TFOAs of 0° , 30° , 45° , 60° , and 90° were enhanced by 65%, 91%, 54%, 66%, and 75%, respectively, under vegetable oil conditions. Erturk et al. (Erturk et al., 2021) did a comparative study of the mechanical and machining performance of polymer hybrid and carbon fiber epoxy composite materials. Although their investigation was focused on dry machining, their major conclusions were centered on the reduction in tool life with dry machining. Hence, the overall increase in machining cost. Similarly, Jemielniak (Jemielniak, 2021) gave some insights into recent research on the machining of some difficult-to-cut materials (which include CFRP) for the aerospace industry. They shared the sentiments of previous authors on delamination on hole surfaces being a major failure arising from the drilling of CFRP composites and suggesting high-performance cooling techniques and hybrid cutting processes as a solution to the bottlenecks. Their work covers cryogenic machining, high-pressure cooling, MQL, and cryogenic MQL cooling. Comparisons of the different cooling techniques are presented in Fig. 4. During dry machining, the cutting area temperature could rise from 200°C to 400°C , which is higher than the glass transition temperature of the matrix (between 80°C and 180°C), resulting in thermal degradation, as well as debonding at the fiber-matrix interface (Jemielniak, 2021).

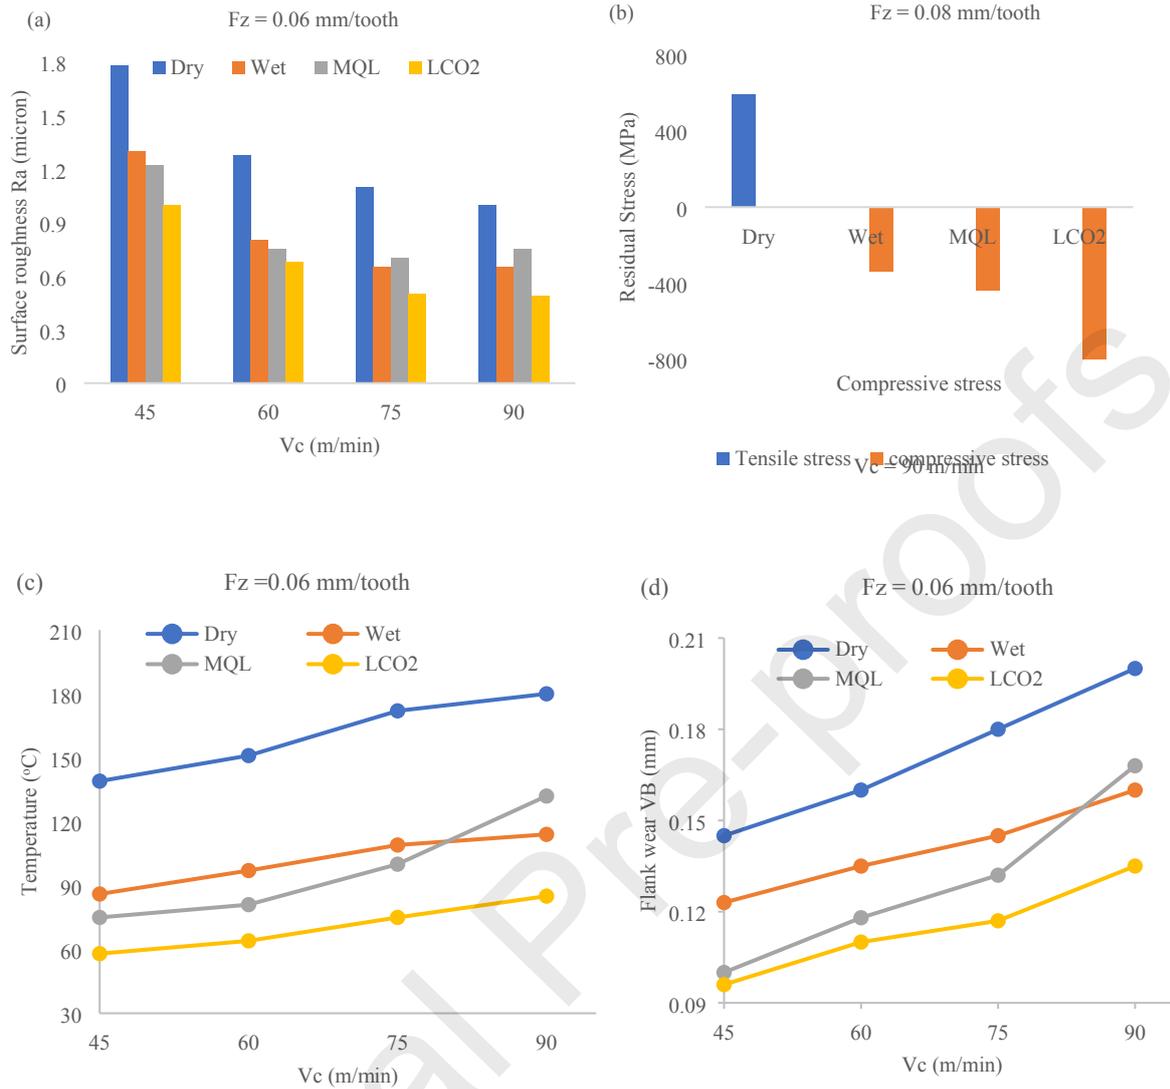


Fig. 4: Results of surface toughness (a), residual stress (b), temperature (c), and wear (d) for different cutting approaches (Jemielniak, 2021)

According to the graphical results presented in Fig. 4, the cryogenic approach to the machining of CFRP is more promising for improved surface finishes compared to other approaches. Because the strategy takes the temperature of the workpiece to the sub-zero zone, cutting temperatures are kept down during the machining process, and tool life is thus improved. In the process, the fillers are stiffened and easily cut, avoiding delamination. Comparatively, dry machining only raises the cutting temperature as the speed increases. The residual stress of different approaches also reduce with the use of nanofluids and is the least with the cryogenic approach.

In spite of the superior properties of nano-based cutting fluids as reported in this review, there are several challenges facing the development and application of nanofluid technology. One of

the major challenges is the long-term stability of NPs in the nanosuspension. One of the most important requirements of the development of nano-based cutting fluids is to ensure that particles (which naturally aggregate due to certain forces including strong van der Waals attraction, drag, thermophoresis, Brownian, and electric double layer forces) attain effective separation in the base oil (Zhao et al., 2021). Another problem is the behavior of nanofluids in turbulent flow. The scarcity of research publications in this area of machining makes it difficult to draw any meaningful conclusion that is expected to serve as guides for future researchers. Nanomaterials are generally not cheap, and the price of NPs is not regulated. According to Kaggwa and Carson (Kaggwa and Carson, 2019), 100 g of Al_2O_3 and CuO nanoparticles, as of 2019, cost \$492 and \$80 respectively. This makes cost another important factor in the synthesis and application of nanofluids.

The general application of nanofluids, considered in its early stages, should lead to increased studies on the potential applications of nanofluids. Scientists and chemists actively participate in the characterization of nanofluids for various applications, while materials and mechanical engineers are fascinated by experiments on the application of nanofluids (Yu et al., 2017). However, there is still a missing common ground that provides general guidelines on the preparation and characterization of stable dispersed thermal nanofluids among these researchers of different disciplines.

7. Conclusion

This review evaluated the formulation of nano-based cutting fluids and their application to carbon fiber-reinforced plastics (CFRPs). It provides a snapshot of current trends in this field by combining and analyzing the latest published literature in the field. The research efforts in this review examined the different methods of cutting fluid preparation as well as a comparative study of conventional approaches to nanofluid preparation (one-step and two-step methods). The two-step approach is gaining more attention from researchers in recent times due to its environmental sustainability potential. The concept of nano Minimum Quantity Lubrication (nMQL) is used for CFRP manufacturing due to the numerous benefits mentioned in recent conversations around the replacement of conventional materials in a wide range of applications. Not only does it reduce the quantity of cutting fluid required for simple drilling, it also promotes the application of CFRPs and motivates future researchers to take a sustainable approach to manufacturing.

Acknowledgment

The authors gratefully acknowledge the financial support from the National Research Fund (NRF) under the aegis of the Tertiary Education Trust Fund (TETFund), Nigeria, (TETF/ES/DR&D/CE/NRF2020/SETI/113/VOL.1), National Research Foundation of South Africa.

Competing interest statement

The authors have no competing interests to declare concerning this manuscript.

References

- Abdalla, M., Dean, D., Theodore, M., Fielding, J., Nyairo, E., Price, G., 2010. Magnetically processed carbon nanotube/epoxy nanocomposites: Morphology, thermal, and mechanical properties, *Polym*, 51(7), 1614–1620. <https://doi.org/10.1016/j.polymer.2009.05.059>.
- Agapiou, J.S., 2018. Performance evaluation of cutting fluids with carbon nano-onions as lubricant additives. *Procedia. Manuf.*, 26, 1429–1440. [doi:10.1016/j.promfg.2018.07.101](https://doi.org/10.1016/j.promfg.2018.07.101).
- Alaboodi, A.S., Sivasankaran, S., Ammar, H.R., 2020. Non-Traditional Machining Process of Composite Materials using Renewable Lubricants, *Int. J. Recent Technol. & Eng. (IJRTE)*, 9(1), 929–933. <https://doi.org/10.35940/ijrte.a1649.059120>
- Ali, A.R.I., Salam, B., 2019. A review on nanofluid: preparation, stability, thermophysical properties, heat transfer characteristics, and application, *SN Appl. Sci.*, 2(10). 1–17. <https://doi.org/10.1007/s42452-020-03427-1>.
- Aramendiz, J., Imqam, A., 2019. Water-based drilling fluid formulation using silica and graphene nanoparticles for unconventional shale applications. *J. Pet. Sci. & Eng.*, 179, 742–749. [doi:10.1016/j.petrol.2019.04.085](https://doi.org/10.1016/j.petrol.2019.04.085).
- Arumugam, S., Ju, Y., 2021 Carbon nanotubes reinforced with natural/synthetic polymers to mimic the extracellular matrices of bone – a review. *Mater. Today Chem.*, 20. [doi 10.1016/j.mtchem.2020.100420](https://doi.org/10.1016/j.mtchem.2020.100420).
- Baskaran, P., Saravanan, R., Vignesh, M., Prasanna, N., Gnanavel, C., Nagarathi, D.K., Gopalakrishnan, T., 2022. Influence of molybdenum disulfide particles' concentration on waste cooking oil nanofluid coolant in cutting force reduction on machining SAE 1144 steel, *Mater. Today: Proceed.*, 2–5. <https://doi.org/10.1016/j.matpr.2022.02.191>.
- Benzait, Z., Trabzon, L.A., 2018. Review of recent research on materials used in polymer–matrix composites for body armor application, *J. Compos. Mater.*, 52(23), 3241–3263. [doi:10.1177/0021998318764002](https://doi.org/10.1177/0021998318764002).
- Bermingham, M.J., Kirsch, J., Sun, S., Palanisamy, S., Dargusch, M.S., 2011. New observations on tool life, cutting forces, and chip morphology in cryogenic machining Ti-6Al-4V. *Int. J. Mach. Tool Manuf.*, 51:500e11. <https://doi.org/10.1016/j.ijmachtools.2011.02.009>
- Bhardwaj, G., 2020. Synthesis and characterization of AL and Cu base nanofluids, *Mater. Today: Proceed.*, 37(Part 2), 3139–3142. [doi: 10.1016/j.matpr.2020.09.039](https://doi.org/10.1016/j.matpr.2020.09.039).

- Bhaumik, S., Paleu, V., Sharma, S., Dwivedi, S., Borkar, S., Kamaraj, M., 2020. Nano and micro additive glycerol as a promising alternative to existing non-biodegradable and skin unfriendly synthetic cutting fluids, *J. Clean Prod.*, 263:121383. <https://doi.org/10.1016/j.jclepro.2020.121383>.
- Bokobza, L., 2019. Natural rubber nanocomposites: A review. In *Nanomaterials*, 9(1), MDPI AG. <https://doi.org/10.3390/nano9010012>.
- Bordin, A., Sartori, S., Bruschi, S., Ghiotti, A., 2017. Experimental investigation on the feasibility of dry and cryogenic machining as sustainable strategies when turning Ti6Al4V produced by Additive Manufacturing, *J. Clean. Prod.*, 142, 4142e51. <https://doi.org/10.1016/j.jclepro.2016.09.209>.
- Borode, A.O., Ahmed, N.A., Olubambi, P.A., Sharifpur, M., Meyer, J.P., 2021. Investigation of the thermal conductivity, viscosity, and thermal performance of graphene nanoplatelet-alumina hybrid nanofluid in a differentially heated cavity, *Frontiers in Energy Res.*, 9, 1–15. doi:10.3389/fenrg.2021.737915.
- Boyoun, N.V., Ismail, I., Wan Sulaiman, W.R., Sharifi Haddad, A., Husein, N., Hui, H.T., Nadaraja, K., 2019. Experimental investigation of hole cleaning in directional drilling by using nano-enhanced water-based drilling fluids, *J. Pet. Sci. & Eng.*, 176, 220–231. <https://doi.org/10.1016/j.petrol.2019.01.063>.
- Che, D., 2014. Machining of carbon fibre reinforced plastics/polymers: a literature review, 136. <https://doi.org/10.1115/1.4026526>.
- Cui, X., Li, Y., Guo, J., Guo, Q., 2021. Fabrication, transport behaviors and green interrupted cutting performance of bio-inspired microstructure on Al₂O₃/TiC composite ceramic surface, *J. Manuf. Proc.*, 75, 203–218. <https://doi.org/10.1016/j.jmapro.2022.01.002>.
- Davim, J.P., Reis, P., 2005. Damage and dimensional precision on milling carbon fiber-reinforced plastics using Design experiments, *J. Mater. Process. Technol.*, 160(2), 160-167.
- Dey, S., Moni Reang, N., Deb, M., Kumar Das, P., 2021. Experimental investigation on combustion-performance-emission characteristics of nanoparticles added biodiesel blends and tribological behaviour of contaminated lubricant in a diesel engine, *Energ. Conv. & Manag.*, 244, 114508. <https://doi.org/10.1016/j.enconman.2021.114508>.
- Dhar, N.R., Kamruzzaman, M., Ahmed, M., 2006. Effect of minimum quantity lubrication (MQL) on tool wear and surface roughness in turning AISI-4340 steel, *J. Mater. Proc. Technol.*, 172(2), 299–304. <https://doi.org/10.1016/j.jmatprotec.2005.09.022>.
- Elgnemi, T., Ahmadi, K., Songmene, V., Nam, J., Jun, M.B.G., 2017. Effects of atomization-based cutting fluid sprays in milling of carbon fibre reinforced polymer composite, *J. Manuf. Proc.*, 30, 133–140. <https://doi.org/10.1016/j.jmapro.2017.09.011>.
- Elgnemi, T.S.M., Jun, M.B.G., Songmene, V., Samuel, A.M., 2021. Milling performance of CFRP composite and atomised vegetable oil as a function of fibre orientation, *Mater.*, 14(8). <https://doi.org/10.3390/ma14082062>.
- Elsheikh, A.H., Elaziz, M.A., Das, S.R., Muthuramalingam, T., Lu, S., 2021. A new optimized predictive model based on political optimizer for eco-friendly MQL-turning of AISI 4340 alloy with nano-lubricants, *J. Manuf. Proc.*, 67, 562–578. <https://doi.org/10.1016/j.jmapro.2021.05.014>.
- Erturk, A.T., Yazar, E., Vatansever, F., Sahin, A.E., Kilinçel, M., Alpay, Y.O., 2021. A comparative study of mechanical and machining performance of polymer hybrid and carbon fibre epoxy composite materials, *Polym. & Polym. Compos.*, 29(9), S655–S666. <https://doi.org/10.1177/096739112111020620>.

- Feito, N., Muñoz-Sánchez, A., Díaz-Álvarez, A. Loya, J.A., 2019. Analysis of the machinability of carbon fiber composite materials in function of tool wear and cutting parameters using the artificial neural network approach, *Materials*, 12, 2747, doi:10.3390/ma12172747.
- Feldman, D., 2017. Natural rubber nanocomposites, *J. Macromolec. Sci., Part A: Pure & Appl. Chem.*, 54(9). <https://doi.org/10.1080/10601325.2017.1316671>.
- Fuskele V., Sarviya R.M., 2017. Recent developments in nanoparticles synthesis, preparation and stability of nanofluids, *Mater. Today Proc.* 4, 4049-4060.
- Gao, T., Zhang, Y., Li, C., Wang, Y., An, Q., Liu, B., Said, Z., Sharma, S., 2021. Grindability of carbon fiber reinforced polymer using CNT biological lubricant, *Scientif. Rep.*, 11(1), 1–14. doi:10.1038/s41598-021-02071-y.
- Gaurav, G., Sharma, A., Dangayach, G.S., Meena, M.L., 2020. Assessment of jojoba as a pure and nano-fluid base oil in minimum quantity lubrication (MQL) hard-turning of Ti–6Al–4V: A step towards sustainable machining, *J. Clean Prod.*, 272, 122553. <https://doi.org/10.1016/j.jclepro.2020.122553>.
- Ghadimi A., Saidur R., Metselaar H.S.C., 2011. A review of nanofluid stability properties and characterization in stationary conditions, *Int. J. Heat Mass Tran.* 54, 4051-4068.
- Ghatge, D.A., Ramanujam, R., Reddy, B.S., Vignesh, M., 2018. Improvement of machinability using eco-friendly cutting oil in turning duplex stainless steel. *Mater. Today: Proceed.*, 5(5), 12303–12310. doi:10.1016/j.matpr.2018.02.208.
- Goindi, G.S., Sarkar, P., 2017. Dry machining: a step towards sustainable machining – challenges and future directions, *J. Clean. Prod.*, 165, 1557–1571. <https://doi.org/10.1016/j.jclepro.2017.07.235>.
- Guo, H., Jerrams, S., Xu, Z., Zhou, Y., Jiang, L., Zhang, L., Liu, L., Wen, S., 2020. Enhanced fatigue and durability of carbon black/natural rubber composites reinforced with graphene oxide and carbon nanotubes, *Eng. Fract. Mechanics*, 223. <https://doi.org/10.1016/j.engfracmech.2019.106764>.
- Guo, Q., Zhang, X.A., 2021. Review of mechanochromic polymers and composites: from material design strategy to advanced electronics application, *Compos. Part B: Eng.*, 227. doi:10.1016/j.compositesb.2021.109434.
- Haq, M.A., Hussain, S., Ali, M.A., Farooq, M.U., Mufti, N.A., Pruncu, C.I., Wasim, A., 2021. Evaluating the effects of nano-fluids based MQL milling of IN718 associated to sustainable productions, *J. Clean. Prod.*, 310, 127463. <https://doi.org/10.1016/j.jclepro.2021.127463>.
- Huang, X., Wu, J., Zhu, Y., Zhang, Y., Feng, X., Lu, X., 2017. Flow-resistance analysis of nano-confined fluids inspired from liquid nano-lubrication: A review, *Chinese J. Chem. Eng.*, 25(11), 1552–1562. doi:10.1016/j.cjche.2017.05.005.
- Jawahar, P., Payak, V., Chandradass, J., Prabhu, P., 2020. Optimization of mechanical properties of CNT-rubber nanocomposites, *Mater. Today: Proceed.*, 45, 7183–7189. doi:10.1016/j.matpr.2021.02.413.
- Jemielniak, K., 2021. Review of new developments in machining of aerospace materials, *J. Machine Eng.*, 21(1), 22–55. <https://doi.org/10.36897/jme/132905>.
- Jia, X. Q., Li, S. Y., Miu, H.J., Yang, T., Rao, K., Wu, D.Y., Cui, B.L., Ou, J.L., Zhu, Z.C., 2020. Carbon nanomaterials: a new sustainable solution to reduce the emerging environmental pollution of turbomachinery noise and vibration. *Frontiers in Chemistry*, 8, 1–6. <https://doi.org/10.3389/fchem.2020.00683>.
- Jose, J., Athikalam Paulose, S., 2020. Studies on natural rubber nanocomposites by incorporating zinc oxide modified graphene oxide, *J. Rubber Res.*, 23(4), 311–321. <https://doi.org/10.1007/s42464-020-00059-3>.

- Kaggwa, A., Carson, J.K., 2019. Developments and future insights of using nanofluids for heat transfer enhancements in thermal systems: a review of recent literature, *Int. Nano Lett.* 9(4), 277–288. <https://doi.org/10.1007/s40089-019-00281-x>.
- Kalla, D., Sheikh-Ahmad, J., Twomey, J., 2010. Prediction of Cutting Forces in Helical End Milling Fibre Reinforced Polymers, *Int. J. Mach. Tools Manuf.*, 50(10), 882-891.
- Karmakar, G., Ghosh, P., Sharma, B.K., 2017. Chemically modifying vegetable oils to prepare green lubricants, *Lubricants*, 5(4), 1–17. <https://doi.org/10.3390/lubricants5040044>.
- Khan, M.M.A., Mithu, M.A.H., Dhar, N.R. 2009. Effects of minimum quantity lubrication on turning AISI 9310 alloy steel using vegetable oil-based cutting fluid, *J. Mater. Proc. Technol.* 209(15–16), 5573–5583. <https://doi.org/10.1016/j.jmatprotec.2009.05.014>.
- Krolczyk, G.M., Maruda, R.W., Krolczyk, J.B., Wojciechowski, S., Mia, M., Nieslony, P., Budzik, G., 2019. Ecological trends in machining as a key factor in sustainable production e A review, *J. Clean. Prod.*, 218, 601-615. <https://doi.org/10.1016/j.jclepro.2019.02.017>.
- Kumar Mishra, S., Ghosh, S., Aravindan, S. 2020. Machining performance evaluation of Ti6Al4V alloy with laser textured tools under MQL and nano-MQL environments, *J. Manuf. Proc.*, 2020;53:174–189. <https://doi.org/10.1016/j.jmapro.2020.02.014>.
- Kumar, A., Sharma, A. K., Katiyar, J. K., 2023. State-of-the-art in sustainable machining of different materials using nano minimum quality lubrication (NMQL), *Lubric.*, 11, 64, 1–30. [doi:10.3390/lubricants11020064](https://doi.org/10.3390/lubricants11020064).
- Kumar, S., Prasad, L., Patel, V.K., Kumar, V., Kumar, A., Yadav, A., Winczek, J. 2021. Physical and mechanical properties of natural leaf fiber-reinforced epoxy polyester composites, *Polym.*, 13(9). MDPI AG. [doi:10.3390/polym13091369](https://doi.org/10.3390/polym13091369).
- Lee, E.S. 2001. Precision machining of glass fiber reinforced plastics with respect to tool characteristics, *J. Adv. Manuf. Technol.*, 17(11), 791-798.
- Li, Z., Xiang, J., Liu, X., Li, X., Li, X., Shan., B. Chen, R., 2022. A combined multiscale modelling and experimental study on surface modification of high-volume micro-nanoparticles with atomic accuracy, *Int. J. Extrem. Manuf.* 4, (025101 (16pp)), <https://doi.org/10.1088/2631-7990/ac529c>.
- Lin, J.L, Su, S.M, He, Y.B., Kang, F.Y., 2020. Improving the thermal and mechanical properties of an alumina-filled silicone rubber composite by incorporating carbon nanotubes, *Xinxing Tan Cailiao/New Carbon Mater.*, 35(1). [https://doi.org/10.1016/S1872-5805\(20\)60476-0](https://doi.org/10.1016/S1872-5805(20)60476-0).
- Ma, C., Wen, R., Zhou, F., Zhao, H., Bao, X., Evelina, A., Long, W., Wei, Z., Ma, L., Liu, J., Chen, S., 2022. Preparation and application of an environmentally friendly compound lubricant based biological oil for drilling fluids, *Arabian J. Chem.*, 15(3), 103610. <https://doi.org/10.1016/j.arabjc.2021.103610>.
- Madanchi, N., Thiede, S., Gutowski, T., Herrmann, C., 2019. Modelling the impact of cutting fluid strategies on environmentally conscious machining systems. *Procedia CIRP*, 80, 150–155. <https://doi.org/10.1016/j.procir.2019.01.068>.
- Mahadi, M.A., Choudhury, I.A., Azuddin, M., Nukman, Y., 2017. Use of boric acid powder aided vegetable oil lubricant in turning AISI 431 steel, *Procedia Eng.* 184, 128–136. [doi:10.1016/j.proeng.2017.04.077](https://doi.org/10.1016/j.proeng.2017.04.077).
- Mahmoud, H., Alhajabdalla, M., Nasser, M.S., Hussein, I.A., Ahmed, R., Karami, H., 2020. Settling behaviour of fine cuttings in fibre-containing polyanionic fluids for drilling and hole cleaning application, *J. Petrol. Sci. & Eng.* 199, 108337. <https://doi.org/10.1016/j.petrol.2020.108337>.

- Makhdoum, B.M., Mahmood, Z., Fadhl, B.M., Aldhabani, M.S., Khan, U., Eldin, S.M., 2023. Significance of entropy generation and nanoparticle aggregation on stagnation point flow of nanofluid over stretching sheet with inclined Lorentz force, *Arabian J. Chem.*, 16(6), 104787. <https://doi.org/10.1016/j.arabjc.2023.104787>.
- Mao, C., Huang, Y., Zhou, X., 2014. The tribological properties of nanofluid used in minimum quantity lubrication grinding, *Int. J. Adv. Manuf. Technol.*, 1221–1228. <https://doi.org/10.1007/s00170-013-5576-7>.
- Maruda, R.W., Legutko, S., Krolczyk, G.M., Raos, P., 2015. Influence of cooling conditions on the machining process under MQCL and MQL conditions, *Tehnicki Vjesnik*, 22(4), 965–970. <https://doi.org/10.17559/TV-20140919143415>.
- Medupin, R.O., Abubakre, O.K., Abdulkareem, A.S., Muriana, R.A., Abdulrahman, A.S., 2019. Carbon nanotube reinforced natural rubber nanocomposite for anthropomorphic prosthetic foot purpose, *Scientif. Rep.*, 9(1) <https://doi.org/10.1038/s41598-019-56778-0>.
- Medupin, R.O., Abubakre, O.K., Abdulkareem, A.S., Muriana, R.A., Kariim, I., Bada, S.O., 2017. Thermal and physico-mechanical stability of recycled high-density polyethylene reinforced with oil palm fibres, *Eng. Sci. & Technol., an Int. J.*, 20(6), 1623–1631. [doi:10.1016/j.jestch.2017.12.005](https://doi.org/10.1016/j.jestch.2017.12.005).
- Mensah, B., Kim, H.G., Lee, J.H., Arepalli, S., Nah, C., 2015. Carbon nanotube-reinforced elastomeric nanocomposites: A review, *Intl J. Smart & Nano Mater.*, 6(4), 211–238. [doi:10.1080/19475411.2015.1121632](https://doi.org/10.1080/19475411.2015.1121632).
- Mirzaasadi, M., Zarei, V., Elveny, M., Alizadeh, S.M., Alizadeh, V., Khan, A., 2021. Improving the rheological properties and thermal stability of water-based drilling fluid using biogenic silica nanoparticles, *Energ. Rep.*, 7, 6162–6171. <https://doi.org/10.1016/j.egy.2021.08.130>.
- Mohammed, L., Ansari, M.N.M., Pua, G., Jawaid, M., Islam, M.S.A., 2015. Review on natural fiber reinforced polymer composite and its applications. *Int. J. Polym. Sci.*, <https://doi.org/10.1155/2015/243947>.
- Ni, J, Cui, Z, Wu, C, Sun, J, Zhou, J. Evaluation of MQL broaching AISI 1045 steel with sesame oil containing nano-particles under best concentration. *Journal of Cleaner Production*, 2021;320:128888. <https://doi.org/10.1016/j.jclepro.2021.128888>.
- Okokpujie, I.P., Tartibu, L.K., 2020. Performance investigation of the effects of nano-additive-lubricants with cutting parameters on material removal rate of al8112 alloy for advanced manufacturing application, *Sustainability (Switzerland)*, 13(15). <https://doi.org/10.3390/su13158406>.
- Olewi, J.K., Hamad, Q.A., Abdulrahman, S.A., 2022. Flexural, impact and max. shear stress properties of fibers composite for prosthetic socket, *Mater. Today: Proceed.*, <https://doi.org/10.1016/j.matpr.2021.12.368>.
- Ouabouch, O., Kriraa, M., Lamsaadi, M., 2021. Stability, thermophysical properties of nanofluids, and applications in solar collectors: A review, 8, 659–684. <https://doi.org/10.3934/matersci.2021040>.
- Padmini, R., Vamsi Krishna, P., Mahith, S., Kumar, S., 2019. Influence of green nanocutting fluids on machining performance using minimum quantity lubrication technique, *Mater. Today: Proceed.*, 18:1435–1449. [doi:10.1016/j.matpr.2019.06.612](https://doi.org/10.1016/j.matpr.2019.06.612).
- Pal, A., Chatha, S.S., Sidhu, H.S., 2021. Performance evaluation of the minimum quantity lubrication with Al2O3-mixed vegetable-oil-based cutting fluid in drilling of AISI 321 stainless steel, *J. Manuf. Proc.*, 66, 238–249. <https://doi.org/10.1016/j.jmapro.2021.04.024>.
- Palanikumar, K., 2008. Application of taguchi and response surface methodologies for surface roughness in machining glass fibre reinforced plastics by PCD tooling, *Int. J. Adv. Manuf. Technol.*, 36(1), 19-27.

- Patole, P.B., Pol, G.J., Desai, A.A., Kamble, S.B., 2021. Analysis of surface roughness and cutting force under MQL turning using nano fluids, *Mater. Today: Proceed.*, 45, 5684–5688. [doi:10.1016/j.matpr.2021.02.501](https://doi.org/10.1016/j.matpr.2021.02.501).
- Pervaiz, S., Kannan, S., Kishawy, H.A., 2018. An extensive review of the water consumption and cutting fluid-based sustainability concerns in the metal cutting sector, *J. Clean. Prod.*, 197, 134–153. <https://doi.org/10.1016/j.jclepro.2018.06.190>.
- Pimenov, D.Y., Mia, M., Gupta, M.K., Machado, A.R., Tomaz, Í.V., Sarikaya, M., Wojciechowski, S., Mikolajczyk, T., Kaplonek, W., 2021. Improvement of machinability of Ti and its alloys using cooling-lubrication techniques: A review and future prospect, *J. Mater. Res. & Technol.*, 2021;11:719–753. [doi:10.1016/j.jmrt.2021.01.031](https://doi.org/10.1016/j.jmrt.2021.01.031).
- Pownraj, C., Valan Arasu, A., 2020. Preparation and characterization of low-cost eco-friendly GAO grafted bio-carbon nanoparticle additive for enhancing the lubricant performance, *Diamond & Related Materials*, 108, 107921. <https://doi.org/10.1016/j.diamond.2020.107921>.
- Pozegic, T.R., Anguita, J.V., Hamerton, I., Jayawardena, K.D.G.I., Chen, J.S., Stolojan, V., Balocchi, P., Walsh, R., Silva, S.R.P., 2016. Multi-functional carbon fibre composites using carbon nanotubes as an alternative to polymer sizing, *Scientif. Rep.*, 6. <https://doi.org/10.1038/srep37334>.
- Rajasekaran, T., Palanikumar, K., Vinayagam, B.K., 2011. Application of fuzzy logic for modelling surface roughness in turning CFRP composites using CBN tool, *Prod. Eng. Res. Dev.* 5(2), 191-199.
- Rapeti, P., Pasam, V.K., Rao Gurram, K.M., Revuru, R.S., 2016. Performance evaluation of vegetable oil-based nano cutting fluids in machining using grey relational analysis-A step towards sustainable manufacturing, *J. Clean. Prod.*, 172, 2862–2875. <https://doi.org/10.1016/j.jclepro.2017.11.127>.
- Sabarinathan, C., Manikandan, N., Sureshkumar, V.P., Siva Murugan, S., Rathis, G., 2020. Effect on tool life by addition of nanoparticles with the cutting fluid, *Mater. Today: Proceed.*, 33, 2940–2954. <https://doi.org/10.1016/j.matpr.2020.02.895>.
- Sahooli M. Sabbaghi S., 2013. CuO nanofluids: the synthesis and investigation of stability and thermal conductivity, *J. Nanofluids*, 1, 155–160.
- Sakthi, S., Hariharan, S.R., Mahendran, S., Azhaganambi, R. 2021. Effect of nano additives on magnesium alloy during turning operation with minimum quantity lubrication, *Mater. Today: Proceed.*, [doi:10.1016/j.matpr2021.04.238](https://doi.org/10.1016/j.matpr2021.04.238).
- Salah, N., Alfawzan, A.M., Saeed, A., Alshahrie, A., Allafi, W., 2019. Effective reinforcements for thermoplastics based on carbon nanotubes of oil fly ash, *Scientif. Rep.*, 9(1) <https://doi.org/10.1038/s41598-019-56777-1>.
- Santhanakrishnan, G. Krishnamurthy, R, Malhotra, S.K., 1992. investigation into the machining of carbon-fibre-reinforced plastics with cemented carbides, *J. Mater. Process. Technol.*, 30(3), 263-275.
- Sarma, P.M.M.S., Karunamoorthy, L., Palanikumar, K., 2008. Modelling and analysis of cutting force in turning of gfrp composites by CBN tools, *J. Reinf. Plast. Compos.*, 27(7), 711-723.
- Sathyanarayana, S. Hübner, C Erratum to: Thermoplastic Nanocomposites with Carbon Nanotubes, 2013; https://doi.org/10.1007/978-3-642-40322-4_13.
- Scholz, M.S., Blanchfield, J.P., Bloom, L.D., Coburn, B.H., Elkington, M., Fuller, J.D., Gilbert, M.E., Muflahi, S.A., Pernice, M.F., Rae, S.I., Trevarthen, J.A., White, S.C., Weaver, P.M., Bond, I.P., 2011 The use of composite materials in modern orthopaedic medicine and prosthetic devices: A review, *Compos. Sci. & Technol.*, 71(16), 1791–1803. [doi:10.1016/j.compscitech.2011.08.017](https://doi.org/10.1016/j.compscitech.2011.08.017).

- Sen, B., Mia, M., Mandal, U.K., Mondal, S.P., 2020. Synergistic effect of silica and pure palm oil on the machining performances of Inconel 690: A study for promoting minimum quantity nano doped-green lubricants, *J. Clean Prod.*, 258, 120755. <https://doi.org/10.1016/j.jclepro.2020.120755>.
- Setti, D., Sinha, M.K., Ghosh, S., Venkateswara Rao, P., 2015. Performance evaluation of Ti-6Al-4V grinding using chip formation and coefficient of friction under the influence of nanofluids, *Int. J. Machine Tools & Manuf.*, 88, 237–248. <https://doi.org/10.1016/j.ijmachtools.2014.10.005>.
- Sezer N., Atieh M.A., Koç M.A., 2019. Comprehensive review on synthesis, stability, thermophysical properties, and characterization of nanofluids, *Powder Technol.*, 344, 404–431.
- Shahnazar, S., Bagheri, S., Abd Hamid, S.B., 2016. Enhancing lubricant properties by nanoparticle additives. *Int. J. Hydrogen Energy*, 41(4), 3153–3170. <https://doi.org/10.1016/j.ijhydene.2015.12.040>.
- Sharma, S.K., Gupta, S.M., 2016. Preparation and evaluation of stable nanofluids for heat transfer application: A review, *Exp. Thermo. Fluid Sci.*, 79, 202-212.
- Sharma, A.K., Tiwari, A.K., Dixit, A.R., 2016. Characterization of TiO₂, Al₂O₃ and SiO₂ Nanoparticle based Cutting Fluids, *Mater. Today: Proceed.*, 3(6), 1890–1898. <https://doi.org/10.1016/j.matpr.2016.04.089>.
- Shokoohi, Y., Khosrojerdi, E., Rassolian Shiadhi, B.H., 2015. Machining and ecological effects of a new developed cutting fluid in combination with different cooling techniques on turning operation, *J. Clean. Prod.*, 94, 330–339. <https://doi.org/10.1016/j.jclepro.2015.01.055>.
- Singh, Y., Farooq, A., Raza, A., Mahmood, M.A., Jain, S., 2017. Sustainability of a non-edible vegetable oil-based bio-lubricant for automotive applications: A review, *Proc. Safety & Enviro. Protection*, 111, 701–713. doi: 10.1016/j.psep.2017.08.041.
- Sofiah, A.G.N., Samykano, M., Pandey, A.K., Kadrigama, K., Sharma, K., Saidur, R., 2021. Immense impact from small particles: review on stability and thermophysical properties of nanofluids, *Sustainable Energy Technol. & Assessments*, 48(5), 101635. <https://doi.org/10.1016/j.seta.2021.101635>.
- Sorrentino, L., Turchetta, S., 2014. Cutting forces in milling of carbon fibre reinforced plastics. 2014.
- Sun, H., Ji, T., Bi, H., Xu, M., Cai, L., Manzo, M., 2021. Synergistic effect of carbon nanotubes and wood-derived carbon scaffold on natural rubber-based high-performance thermally conductive composites. *Compos. Sci. & Technol.*, 213. <https://doi.org/10.1016/j.compscitech.2021.108963>.
- Tasdelen, B., Wikblom, T., Ekered, S., 2008. Studies on minimum quantity lubrication (MQL) and air cooling at drilling, *J. Mater Proc Technol*, 200(1–3), 339–346. <https://doi.org/10.1016/j.jmatprotec.2007.09.064>.
- Taureza, M., Song, X., Castagne, S., 2014. On the influence of workpiece material on friction in micro forming and lubricant effectiveness, *J. Mater. Process. Technol.*, 214, 998–1007. <https://doi.org/10.1016/j.jmatprotec.2013.11.003>.
- Tran Minh Duc, TTL, TQC., 2019. Performance evaluation of MQL parameters using Al₂O₃ and MoS₂ nanofluids in hard turning 90CrSi steel, *Lubricants*, 7, 1–17. <https://doi.org/10.3390/lubricants7050040>.
- Uhlmann, E., Sammler, F., Richarz, S., Heitmüller, F., Bilz, M., 2014. Machining of carbon fibre reinforced plastics, *Procedia CIRP*, 24, 19–24. <https://doi.org/10.1016/j.procir.2014.07.135>.
- Urmi, W.T., Shafiqah, A.S., Rahman, M.M., Kadrigama, K., Maleque, M.A., 2021. Preparation methods and challenges of hybrid nanofluids: a review, *J. Adv. Res. in Fluid Mechanics & Thermal Sci.*, 78(2), 56–66. <https://doi.org/10.37934/ARFMTS.78.2.5666>.

- Usha, M., Srinivasa Rao, G., 2019. Optimisation of parameters in turning using herbal based nano cutting fluid with minimum quantity lubrication, *Mater. Today: Proc.*, 22, 1535–1544. doi:10.1016/j.matpr.2020.02.115.
- Veeman, D., Shree, M.V., Sureshkumar, P., Natrayan, L., Ravichandran, M., Paramasivam, P., 2021. Sustainable development of carbon nanocomposites: synthesis and classification for environmental remediation, *J. Nanomater.*, Hindawi Limited. <https://doi.org/10.1155/2021/5840645>.
- Venkatesh, K., Sriram, G., Uday Kiran Reddy, A., Nikhil, S.V.R., 2018. Influence of nano-based metal working fluids on machining process - A Review. *IOP Conf. Ser.: Mater. Sci. & Eng.*, 390(1). <https://doi.org/10.1088/1757-899X/390/1/012094>.
- Virdi, R.L., Chatha, S.S., Singh, H., 2020. Performance evaluation of inconel 718 under vegetable oils based nanofluids using minimum quantity lubrication grinding, *Mater Today: Proc.* 33, 1538–1545. doi:10.1016/j.matpr.2020.03.802.
- Wang, W., Zhu, Y., Liao, S., Li, J., 2014. Carbon nanotubes reinforced composites for biomedical applications, *BioMed Res. Int.*, Hindawi Publishing Corporation. <https://doi.org/10.1155/2014/518609>.
- Wickramasinghe, K.C., Sasahara, H., Rahim, E.A., Perera, G.I.P., 2020. Recent advances on high performance machining of aerospace materials and composites using vegetable oil-based metal working fluids, *J. Clean Prod.* 310, 127459. <https://doi.org/10.1016/j.jclepro.2021.127459>.
- Yu, F., Chen, Y., Liang, X., Xu, J., Lee, C., Liang, Q., Tao, P., Deng, T., 2017. Dispersion stability of thermal dispersion stability of thermal nanofluids, *Prog. Nat. Sci. Mater. Int.* 27, 531–542. <https://doi.org/10.1016/j.pnsc.2017.08.010>.
- Zaaba, N.F., Ismail, H., 2019. Thermoplastic/natural filler composites: A short review, *In J. Physical Sci.*, 30, 81–99. <https://doi.org/10.21315/jps2019.30.s1.5>.
- Zadafiya, K., Shah, P., Shokrani, A., Khanna, N., 2021. Recent advancements in nano-lubrication strategies for machining processes considering their health and environmental impacts, *J. Manuf. Proc.*, 68(PA), 481–511. <https://doi.org/10.1016/j.jmapro.2021.05.056>.
- Zhang, Y., Li, C., Jia, D., Zhang, D., Zhang, X., 2015. Experimental evaluation of MoS₂ nanoparticles in jet MQL grinding with different types of vegetable oil as base oil, *J. Clean. Prod.*, 87, 930–940. <https://doi.org/10.1016/j.jclepro.2014.10.027>.
- Zhao, J., Gao, T., Li, Y., He, Y., Shi, Y., 2021. Two-dimensional (2D) graphene nanosheets as advanced lubricant additives: A critical review and prospect, *Mater. Today Comm.*, 29, 102755. doi:10.1016/j.mtcomm.2021.102755.
- Zhu, H.T., Lin, Y.S., Yin, Y.S., 2004. A novel one-step chemical method for preparation of copper nanofluids. *J. Colloid & Interface Sci.*, 277(1), 100–103. <https://doi.org/10.1016/j.jcis.2004.04.026>.
- Zwawi, M., 2021. A review on natural fiber bio-composites, surface modifications and applications, *Molecules*, 26(2), doi:10.3390/molecules26020404.

18th November

2022

The Editor-in-Chief,

Arabian Journal of Chemistry

Dear Editor-in-Chief,

Conflict of interest Declaration

All authors unanimously declare that there is no conflict of interest in the publication of this manuscript.

Thank you in anticipation of your favorable response to our submission.



Yours sincerely,

Dr. Kelvin O. Yoro (Corresponding Author)