



EFFECT OF PARTIAL REPLACEMENT OF FINE AGGREGATE WITH SAWDUST IN LIGHT WEIGHT CONCRETE PRODUCTION USING BIDA NATURAL STONE AS COARSE AGGREGATE

Alhaji B.¹, Abubakar M.¹, Yusuf A.¹, Oritola S. F.¹, Mohammed S.¹ and Kolo D. N.¹

¹Department of Civil Engineering, Federal University of Technology, Minna
E-mail: balhaji180@yahoo.com

ABSTRACT

This study investigated the effect of sawdust as partial replacement for Fine Aggregate in light weight concrete production. Sawdust was used to replace Fine Aggregate from 0% to 40% in steps of 5%. 150 x 150 x 150mm concrete cubes were cast for each replacement level, the concrete was cured and the compressive strengths were determined at 7, 21 and 28 days curing period respectively. Increase in percentage of sawdust in concrete led to a constant reduction in the compressive strength values with a corresponding reduction in weight. From the result obtained, 5% replacement of Fine Aggregate with sawdust gave a maximum compressive strength 13.11 N/mm². It was however concluded that the optimum replacement level of 5% can be used as plain concrete for blinding works.

Keywords: Bida, Compressive Strength, Light Weight Concrete, Sawdust

1. INTRODUCTION

The overall relevance of concrete in virtually all Civil Engineering Practice and Building Construction Works cannot be overemphasized (Adewuyi and Adegoke, 2008). Concrete is a combination of cement, aggregates and water, which are mixed in a right proportion to arrive at the strength. The cement and water react together chemically to form a paste, which binds the aggregate particles together. The mixture sets into a rock-like solid mass, which has considerable compressive strength but little resistance to tension (Agbede and Menessh, 2009). However, the construction industry relies heavily on conventional materials such as cement, granite and sand for the production of concrete. The high and increasing cost of these materials has greatly hindered the development of shelter and other infrastructural facilities in developing countries (Olutoge, 2010). Scientists,

Engineers and Technologists are continuously on the lookout for new materials which can be used as substitutes for conventional materials, especially where their properties would enable their use in new designs and innovative applications. There is also an increasingly awareness of the need to re-use or recycle waste. The growing concern of resource depletion and global pollution has challenged many researchers and engineers to seek and develop new materials relying on renewable resources. These include the use of by-products and waste materials in building construction. Many of these by-products are used as aggregates for the production of light weight concrete (Adewuyi and Adegoke, 2008). The most widely used fine aggregate for the making of concrete is the natural sand mined from the river beds. However, the availability of river sand for the preparation of concrete is becoming scarce due to the excessive nonscientific methods of mining from the river beds, lowering of water table and sinking of the bridge piers among others, is becoming common treats (Mageswari and Vidivelli, 2010). The Worldwide consumption of sand as fine aggregate in concrete production is very high and



Several developing countries have encountered some strain in the supply of natural sand in order to meet the increasing needs of infrastructural development in recent years (Shrivastava *et al.*, 2012). Simultaneous accumulation of unmanaged wastes especially in developing countries has resulted in an increasing environmental concern. However, the increase in the popularity of using environmental friendly, light weight construction materials in building industry has brought about the need to investigate how this can be achieved by benefiting environment as well as maintaining the material requirements affirmed in the standards. Sandwast is an industrial waste in the timber

industry constitute a nuisance to both the health and environment when not properly managed (Eshuwa and Adedokun, 2011). Wood sandwast wastes are accumulated from the countries all over the world and cause certain serious environmental problems and health hazards. Generation of wood waste in itself is an unavoidable hence a great efforts are made in the utilization of such waste (Lizoval *et al.*, 2016). Thus, this research investigates the potential use of wood sandwast wastes to produce a low cost and light weight concrete for construction and engineering purposes.

2. MATERIALS AND METHOD

2.1 Sourcing of materials

The sandwast for this study was collected from a saw mill point at Cridan Kwarin, opposite Federal University of Technology Minna, Niger State Nigeria. The sample was carefully collected to avoid mixing with the sand. The natural stones of maximum size of 25mm used as coarse aggregate were obtained from Bida Niger state, Nigeria. Natural sand (having smooth and more rounded particles) passing sieve 5mm and used was collected from a river bed at Cridan Kwarin road, Federal University of Technology Minna, Niger State. For use in this concrete production, it was ensured that the sand was clean, sound and well graded according to requirement set by BS12, 1994. Ordinary Portland cement (OPC) conforming to BS12, 1994 was used.

Trassite was used being the most widely recommended material of its kind. Bags of the cement were brought at a retail store in Minna, Niger State.

The water which is used for mixing the materials was obtained from a borehole at Cridan Kwarin Campus which conforming to BS142 (1976) requirements. Therefore, the water is fit for drinking, free from suspended particles and organic materials which might affect hydration of cement.

2.2 Sample preparation

Prior to mixing of the concrete components, tests such as specific gravity tests, moisture content, particle size analysis, loose and compacted bulk density tests, mass absorption of aggregates were conducted on sand, saw dust and gravel. Fine aggregate, cement, sandwast, and water were mixed to form a paste (in which slump and compacting factor tests was conducted) which used to fill the voids around coarse aggregates. A chemical process called hydration occurred which transformed the semi liquid mass into a hard, strong engineering material. In this investigation, sandwast was used as partial replacement for the fine aggregate (sand). This work attempts to establish that the mixture of cement, sand - sandwast and gravel might have an equal advantage as its standard mix of cement, sand and gravel. Both mix are in the proportion 1: 2: 6 (Cement, fine aggregate and coarse aggregate) respectively. Eighty one cubes were cast with the same volume proportions. After placing in 150 x 150 x 150mm moulds, they were left to set for 24 hours, and kept afterwards in a curing tank. The cured samples were tested after 7, 21 and 28 days for compressive strengths in accordance with BS1221, 1975.

3.0 RESULTS AND DISCUSSION

Table 1: Physical properties of Constituent Materials

Properties	Sawdust	Sand	Gravel
Loose bulk density (g/cm ³)	1.225	1.264	1.367
Compacted bulk Density (g/cm ³)	1.414	1.415	1.488
Water content (%)	7.79	6.19	1.57
Water absorption (%)	14.95	13.55	5.07
Specific gravity	1.37	2.66	2.17

Specific gravity value of 1.37 place the sawdust in the same category as lightweight aggregate while the specific of the sand and the gravel place them in the category of common rock group whose gravities range from 2.62- 3.00 (Neville, 2000). However, the loose and compacted bulk densities for both

Sawdust and that of sand are relatively the same, which makes the two material complimentary. Saw dust was found to have a greater water content value than sand with the difference in the region of 0.19%. This, thus, will cause a reduction in the workability of the fresh concrete.

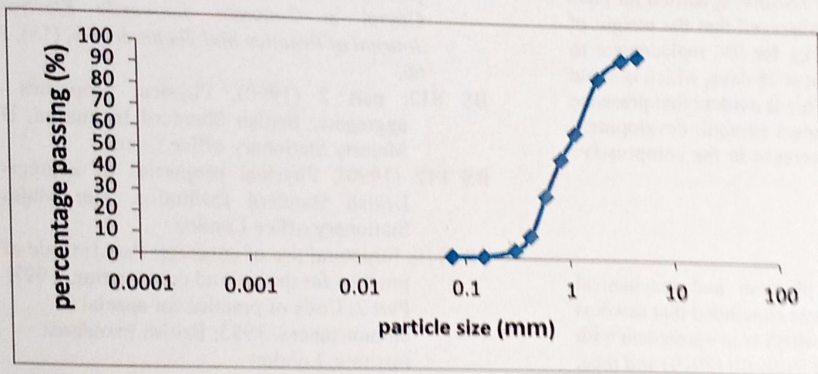


Figure 1: Particle Size Distribution Curve for Saw dust

It can be seen from the particle size distribution that the sawdust can act as sand and even as minerals fillers by virtue of the distribution.



Table 2: Result of Compressive Strength Test

% Replacement	7 Days Curing	21 Days Curing	28 Days Curing
0	15.69	21.82	26.27
5	9.20	12.58	13.11
10	6.31	5.73	7.4
15	4.09	5.20	5.42
20	2.98	4.13	5.40
25	2.76	3.02	3.24
30	2.40	2.76	2.93
35	2.09	2.31	2.53
40	1.60	2.13	2.22

It is seen from Table 2 that for control cube, the compressive strength increased from 15.69N/mm² at 7days to 26.27N/mm² at 28 days (about 10.58% increment). This is equivalent to grade 25 concrete that has a specified value of 25N/mm² (BS 8110, 1997). The 10% replacement sample gave a value of 7.4N/mm² at 28days which is equivalent to grade 7 concrete that has a value of 7N/mm² specified for plain concrete. It could also be observed that the weight of the cube reduced from 8.5kg for 0% replacement to 7.53kg for 10% replacement at 28 days, which is about 20% reduction in weight. This is evident that presence of sawdust in concrete hinders strength development of cement, thus causing decrease in the compressive strength.

4. CONCLUSION

From the results of the physical and mechanical property test conducted, it was concluded that sawdust is a light weight aggregate which is in agreement with the work of Mageswari and Vidivelli (2010) and thus, could be used as partial replacement for sand in plain concrete for blinding work.

However, to achieve best result in the use of sawdust in concrete production, optimum replacement level of 5% is recommended. It is also recommended that further works should be conducted with varying w/c ratios to determine the optimum.

REFERENCES

- Adewuyi A.P & adegoke T., (2008). Exploratory study of periwinkle shells as coarse aggregate in concrete works. *Journal of Applied Sciences Research*, 4 (12), 1678-1681.
- Agbede O.I and Monash J. (2009). Suitability of periwinkle shell as partial Replacement for Gravel in Concrete. *Leonardo Electronic Journal of Practice and Technologies*, (15), 56-66.
- BS 812: part 2 (1990), Physical properties of aggregate. British Standard Institution, Her Majesty Stationary office London
- BS 812 (1990), Physical properties of aggregate. British Standard Institution, Her Majesty Stationary office London
- BS 8110: Structural use of concrete; Part 1: Code of practice for design and construction, 1997; Part 2: Code of practice for special circumstances, 1985; British Standards Institute, London
- BS 1881 Part 116 (1983). Method for Determining Compressive Strength of Concrete Cubes. British Standard Institution, Her Majesty Stationary office London
- BS 3148 (1980). Specification for concrete water. British Standard Institution, Her Majesty Stationary office London
- Divatar Y., Manjunath S., & Aswath M. U., (2012). Experimental Investigation on Behaviour of Concrete Fines. *International Journal of Advance Engineering Research*, 1 (4), 23-30
- Elinwa A.U & Abdulkadir S., (2011). Characterizing Saw Dust Ash for Use as an Inhibitor for Reinforcement Corrosion. *New Clues in Sciences*, 1, 1-10



- Mageswari M. & Vidivelli B., (2010). The Use of Sawdust Ash as Fine Aggregate Replacement in Concrete. *Journal of Environment Research and Development*, 3 (3), 720-726.
- Mageswari M. & Vidivelli B., (2010). The Use of sheet Glass Powder as Fine Aggregate Replacement in concrete. *The open Civil Engineering Journal*, 4, 65-71.
- Marthong C. (2012). Size Effect study of Saw Dust Ash Concrete under compressive load. *IOSR Journal of mechanical and Civil Engineering (IOSRJMCE)*, 2(5), 27-32.
- Murali G. & Ramkumar V.R. (2012). Properties of Concrete with partial Replacement of Coarse Aggregate. *International Journal of Emerging Trends in Engineering and Development*, 4 (2), 585-589.
- Neville A.M. (2000). *Properties of Concrete*. 4th Edition, Pitman Publishing Ltd, 39 parker Street, London
- Olotoye F.A (2010). Investigations on Sawdust and Pam kernel Shells as Aggregate Replacement. *ARPN Journal of Engineering and Applied Sciences*, 5 (4) 8-12.
- Turgut P. & Algin M.H. (2012). Lime Dust and Wood Sawdust as Brick Materials. *Building and the Environment*. 42, 3399-3403.
- Turgut P. (2007). Cement Composite with Limestone Dust and Different Grades of Wood Sawdust. *Building and Environment*, 42, 3801-3807